



Revision of EU European Ecolabel for Indoor and Outdoor Paints and Varnishes

EU Ecolabel Criteria Proposal Report

Giannis S. Kougoulis, Renata Kaps,
Ben Walsh

July 2012

Glossary

Units Conventional SI units and prefixes used throughout: {k, kilo, 1000} {M, mega, 1,000,000} {G, giga, 10^9 } {kg, kilogramme, unit mass} {t, metric tonne, 1,000 kg}

Acknowledgements

The authors would like to thank all the stakeholders who contributed to drafting this document.

Contents

1	Introduction	3
2	Scope	4
2.1	Merging indoor and outdoor paints, and changing the scope of the documents	4
2.2	Aim of the criteria and framework	5
2.3	Criteria Decision: Article 1 (Scope)	7
3	Production	11
3.1	Raw material sourcing	11
4	Use	16
4.1	Efficiency in use	16
4.2	Emissions during use	23
5	End of life	48
5.1	Unused paint disposal	48
5.2	Packaging material	49
6	General	51
6.1	Consumer information	51
6.2	Information appearing on the Ecolabel	51
6.3	General comment	52
7	Criteria	52

1 Introduction

The European Ecolabel is an element of the European Commission's action plan on Sustainable Consumption and Production and Sustainable Industrial Policy Consumption and Production and Sustainable Industrial Policy adopted on 16 July 2008. This is a voluntary scheme established to encourage manufacturers to produce goods and services that are environmentally friendlier. The EU Ecolabel flower logo should facilitate recognition by consumers and organizations (i.e. public and private purchasers) of the best performing products in this respect, and making environmentally conscious choices more easily. The EU Ecolabel covers a wide range of products and services, and its scope is constantly being broadened. The process of establishing the criteria proceeds at the European level following consultation with experts and all interested parties. A product or a service awarded with this label must meet high environmental and performance standards.

This document details discussion points and specific evidence for amending or adding to the current EU Ecolabel paints and varnishes. It relies on the evidence base described within the following reports:¹ *"Ecolabel and Green Public Procurement (GPP) Criteria for Paints and Varnishes: Preliminary Background Report"*, and *"Ecolabel Criteria for Paints and Varnishes: Background Report"* and the feedback received from stakeholders and from the 1st Ad-Hoc Working Group (AHWG).

This document sets out the rationale for updating the current EU Ecolabel criteria for paints and varnishes and provides an updated criterion at the end of each section (within blue boxes). The final section provides complete EU Ecolabel criteria proposed for paints and varnishes.

¹ Reports are available via the project website: <http://susproc.jrc.ec.europa.eu/paints/stakeholders.html>

2 Scope

2.1 Merging indoor and outdoor paints, and changing the scope of the documents

It has become clear that some paints have both indoor and outdoor applications and as such require two licences. Discussions with applicants and other stakeholders, in addition to experience from the current EU Ecolabel paints and varnishes assessment process, confirms this. Applying for two separate licences for a single product adds additional cost and administrative burden to the applicant company and can confuse consumers. Of particular concern is that a paint passing both sets of criteria could display two licence numbers and two EU Ecolabels: having two licences could be interpreted as 'better' than having one. The merger of the two criteria documents was thus proposed to stakeholders. The overall aim is the production of a document that covers indoor paints, outdoor paints and also paints that can comply with both indoor and outdoor criteria. Only relatively minor changes to each criteria would be needed to realise this modification.

In general, stakeholders responded positively to the idea of combining the two criteria: such a merger was anticipated to reduce confusion among customers and applicants, while minimising administrative burden for both competent bodies and applicants. As a concern it was raised, however, that the merger might result in a reduction of income for competent bodies.

With this in mind, the Indoor and Outdoor Paint and Varnishes Criteria have been merged. The following sections examining the current criteria have been framed to incorporate the necessary changes allowing the combination of the documents that previously separately covered indoor and outdoor paints and varnishes.

2.2 Aim of the criteria and framework

This part of the criteria decision remains in general as it is in the current criteria decisions for indoor and outdoor paints. A small amendment is also proposed regarding the ingoing substances following parallel developments of EU Ecolabel criteria decisions in other product groups.

The following text is proposed:

Criteria aim

The criteria aim, in particular at promoting:

- products that have a lower environmental impact along their life cycle,
- products which contain a limited amount of hazardous substances
- products which emit a reduced amount of volatile organic compounds
- indoor products which ensure a higher indoor air quality
- the efficient use of the product and the minimization of waste

Criteria

Criteria are set for each of the following aspects:

1. Production phase -Raw material sourcing
2. Use phase
 - i) Efficiency in use
 - ii) Emissions during use
3. End of life phase
 - i) Unused paint disposal
 - ii) Packaging material
4. Consumer information- Information appearing on the Ecolabel

(1) Assessment and verification

(a) Requirements

The specific assessment and verification requirements are indicated within each criterion.

Where the applicant is required to provide declarations, documentation, analyses test reports or other evidence to show compliance with the criteria, it is understood that these may originate from the applicant and/or his supplier(s) and/or their supplier(s), et cetera, as appropriate.

Where possible, the testing should be performed by laboratories that meet the general requirements of EN ISO 17025 or equivalent.

Where appropriate, test methods other than those indicated for each criterion may be used if the competent body assessing the application accepts their equivalence.

Where appropriate, competent bodies may require supporting documentation and may carry out independent verifications. The competent bodies are recommended to take into account the implementation of recognised environmental management schemes, such as EMAS or EN ISO14001, when assessing applications and monitoring compliance with the criteria (*Note: it is not required to implement such management schemes*).

(b) Measurement thresholds

Unless otherwise indicated compliance with the ecological criteria is required for substances intentionally added, as well as for by-products and impurities from raw materials, the concentration of which equals or exceeds 0,010 % by weight of final formulation.

(2) Functional unit and reference flow

The reference flow for the functional unit of this product group is the amount of paint required to cover a 20 m² surface to a 98% opacity. The ingoing substances shall be also expressed in g of ingredient per amount of paint required to cover a 20 m² surface to a 98% opacity.

The exact formulation of the product (trade name, chemical name, CAS no.), the function and the form of all the ingoing substances (regardless of concentration) that are used by the applicant as well the ingoing quantity including and excluding water or solvent should be provided to the competent body. Any substance, including impurities, present in concentrations greater than 0,01 % (m/m) should be reported unless a lower concentration is specified elsewhere in the criteria.

Where ingredients are referred to in the criteria, this includes substances and preparations. The definitions of 'substances' and 'preparations' are given in the REACH Regulation (Regulation (EC) No 1907/2006 of the European Parliament and of the Council (1).

Safety data sheets for each ingoing substance shall be submitted to the competent body in accordance with Regulation (EC) No 1907/2006 of the European Parliament and of the Council.

2.3 Criteria Decision: Article 1 (Scope)

During the implementation and use of the EU Ecolabel, several questions on the scope of the criteria have been raised. Table 1 summarises the proposed amendments, stakeholder feedback (from the initial survey and the 1st AHWG) and provides guidance on a decision for inclusion or rejection from the Ecolabel.

There were requests to clearly define the terms ‘transparent’ and ‘semi-transparent’. Information provided by stakeholders states that semi-transparent products’ pigments are non-white², which increases the paint’s opacity but does not result in it being completely opaque. Transparent paints do not contain any pigment. This is of particular importance for paints that contain only a small amount of TiO₂ (white pigment) for classification and assessment under Criterion Numbers 1 and 2. The following clarification has been proposed by stakeholders and included in the amended criterion:

Transparent and semi-transparent should add a contrast ratio of:

Transparent < 90% at 120μ

Semi Transparent 90-98% at 120μ

Opaque > 98% at 120μ.

Confusion exists over the terminology for ‘primers’ and ‘undercoats’. These terms are often considered, erroneously, as synonymous. The following clarifications from Annex I of Directive 2004/42/CE: “on the limitation of emissions of volatile organic compounds due to the use of organic solvents in certain paints and varnishes and vehicle refinishing products” are now included within the text:

1.1.d:

d) ‘interior/exterior trim and cladding paints for wood, metal or plastic’ means coatings designed for application to trim and cladding which produce an opaque film. These coatings are designed for either a wood, metal or a plastic substrate. This subcategory includes undercoats and intermediate coatings

1.1.g:

‘primers’ means coatings with sealing and/or blocking properties designed for use on wood or walls and ceilings.

Stakeholders were in general in agreement with the use of these clarifications, although some were concerned that definition 1.1.g could be considered as too narrow.

² A small amount of white pigment is sometimes used in some semi-transparent paints.

Table 1: Discussion of changes to the scope of the EU Ecolabel and comments from stakeholders

Product	Discussion	Stakeholder feedback	Recommendation
Wood oils	These treatments for wood penetrate the wood's surface and are arguably different than varnishes. Wood oils are mainly solvent-based and require a significant variation on the amount of allowable VOC to be permitted. These products penetrate the wood rather than forming a solid surface and are sometimes not classified as paints under the current definition. Also, the discussion at the AHWG for revision of this criteria in 2007 concluded that they should be omitted	Mixed views	Exclude but propose to include in the Commission's recommendation letter for investigation in the next criteria revision
UV curable paints	These specialist paints are in wide use, however are not readily available on the domestic market. They also require specialised equipment during application.	Unanimous exclude	Exclude
Powder coatings/paints	These are currently specified within scope, however, they face similar concerns as UV curable paints over availability on the market and use by non-industrial users. They are technical paints usually applied in an industrial setting requiring ovens to cure the paints.	Unanimous exclude	Exclude
Anti corrosive metal primers and topcoats	Stakeholders indicate that many of these products are specialised for industrial uses and would generally fail EU Ecolabel standards. Some argue that the less active water-based products should be included.	Mixed views	Include but final resolution to be made at the next AHWG. In case of inclusion we propose an additional fitness for use criterion.
Non film forming coatings (eg stone protection materials)	This class of products does not form a film and are therefore excluded under the criterion selection.	Mixed views	Exclude but final resolution to be made at the next AHWG
Preparation products (like filling putties for holes, cracks)	The explicit exclusion of facade coating from the current criteria suggests that similar products such as filling putties should also be excluded.	Mixed views	Exclude but propose to include in the Commission's recommendation letter for investigation in the next criteria revision
Thick waterproofing and insulation coatings for outdoor uses	A lack of suitable spreading-rate criterion currently prevents their inclusion, and, therefore, the development of an appropriate clause under spreading rates is required.	No or weak responses	Exclude but guidance is needed from the next AHWG
Parquet and floor waxes	These form solid transparent films on wood floors. Although scope exists for inclusion within the current document, (through articles 1 & 2) and could be considered as a varnish, the Competent Body Forum on June 2011 excluded these products due to the fact that they have not been considered during development of the current criteria.	Mixed views. Weak positive responses.	Exclude but propose to include in the Commission's recommendation letter for investigation in the next criteria revision
Façade coatings	Façade coatings are currently excluded from the criteria of paints for indoor use but are included in the outdoor.	No response	Exclude but guidance is needed from the next AHWG.
Paints used for street marking	Typically this product is not purchased by private consumers. However, as it is considered highly relevant for the scope of the Green Public Procurement criteria, for the sake of consistency, it could be considered to include also in Ecolabel. Comments for a definition proposal from stakeholders are welcome.	Unanimous exclude	Exclude

The below section gives details of the updates of the EU Ecolabel Paints and Varnishes scope and definitions.

The product group 'paints and varnishes' shall comprise **both indoor and outdoor** decorative paints and varnishes, woodstains and related products, as defined in paragraph 2, intended for use by do-it-yourself and professional users (**please note that these are not industrial users**).

This includes, inter alia, floor coatings and floor paints, products which are tinted by distributors at the request of amateur or professional decorators, tinting systems, decorative paints in liquid or paste formulas which may have been pre- conditioned, tinted or prepared by the manufacturer to meet consumer's needs, including **wood paints, wood and decking stains, masonry coatings and metal finishes** primers and undercoats of such product systems as defined within **Directive 2004/42/CE Annex I 1.1.d and 1.1.g**.

Definitions

'Paint' means a pigmented coating material, in liquid or in paste form, which when applied to a substrate, forms an opaque film having protective, decorative or specific technical properties.

'Varnish' means a clear coating material which when applied to a substrate forms a solid transparent film having protective, decorative or specific technical properties.

After application, the paint or varnish dries to a solid, adherent and protective coating.

'Decorative paints and varnishes' means paints and varnishes that are applied to buildings, their trim and fittings, for decorative and protective purposes. They are applied in-situ. While their main function is decorative in nature, they also have a protective role.

'Woodstains' (lasures) means coatings producing a transparent or semi-transparent (**using substantially non-white pigment**) film for decoration and protection of wood against weathering, which enables maintenance to be carried out easily.

'Tinting systems' is a method of preparing coloured paints by mixing a 'base' with coloured tints.

Masonry coatings are coatings that produce a decorative and protective film for use on concrete, (paintable) brickwork, blockwork, rendering, calcium silicate or fibre-reinforced cement. They are intended principally for exterior use, but may also be used internally, or on soffits and balcony ceilings.

The following definitions shall be used:

Transparent: contrast ratio < 90% at 120 μ ;

Semi Transparent: contrast ratio 90-98% at 120 μ ;

Opaque contrast: ratio >98% at 120 μ .

White and light coloured paints are those with a tri-stimulus (Y-value) >70%

3. The product group shall not comprise:

- a) anti-fouling coatings
- b) wood preservation products
- c) coatings for particular industrial and professional uses, including heavy-duty coatings
- d) **facade coatings**
- e) Powder coatings
- f) UV curable paint systems
- g) Paints primarily intended for vehicles
- h) products that do not form film over the substrate.

3 Production

3.1 Raw material sourcing

3.1.1 White Pigments

A reduction in the use of pigment in paints, particularly titanium dioxide, is desirable because it is a major contributor to the paint's environmental impact. Pigment has an effect on the opacity of paint, therefore any reduction in use must be balanced against a reduction in the performance. Paint spreading performance is defined within the Spreading Rate criterion and is directly linked to the amount of pigment added to the paint. Alterations to the Spreading Rate Criterion along with this criterion should be considered in parallel to ensure that any changes do not prove too restrictive. To simplify this problem, the thresholds for the spreading rate will be held at their current levels and that changes are made to this criterion.

Respondents to the survey, mainly from industry, stated that the current requirements are difficult to meet and that any further tightening would significantly impact on the quality of the paint. To evaluate this response, anonymised data were received from approved EU Ecolabel applications from competent bodies. These data provided performance information on successfully Ecolabelled products. A comparison between the amount of white pigment required by EU Ecolabelled paints and the criterion limit was performed. Table 2 summarises these results.

Table 2: Amount of TiO₂ per m² of EU Ecolabelled paints

Type	Number of paints	Average white pigment (g/m ²)	Standard deviation (g/m ²)	Current threshold (g/m ²)
Indoor	58	23.5	8.6	36
Outdoor	12	18.1	13.3	38

Based on the data collected, current EU Ecolabelled products perform significantly better than those defined by the criteria for both indoor and outdoor paints. Analysis of the cumulative frequency shows that amounts of titanium dioxide vary in submitted paints, with only a small proportion of paints having greater than 30g/m² of white pigment (Figure 1). Stakeholder feedback stated that these figures are low, and that the amount of TiO₂ in paint in Southern Europe is considerably higher.

Stakeholders claim that the lower levels of TiO₂ are due to a large number of matt wall emulsions that are Ecolabelled rather than higher performing paints. Further analysis of the paints with higher concentrations of white pigment is limited due to confidentiality; therefore, verifying stakeholder claims that high scrub resistance paints cannot be Ecolabelled was not possible.

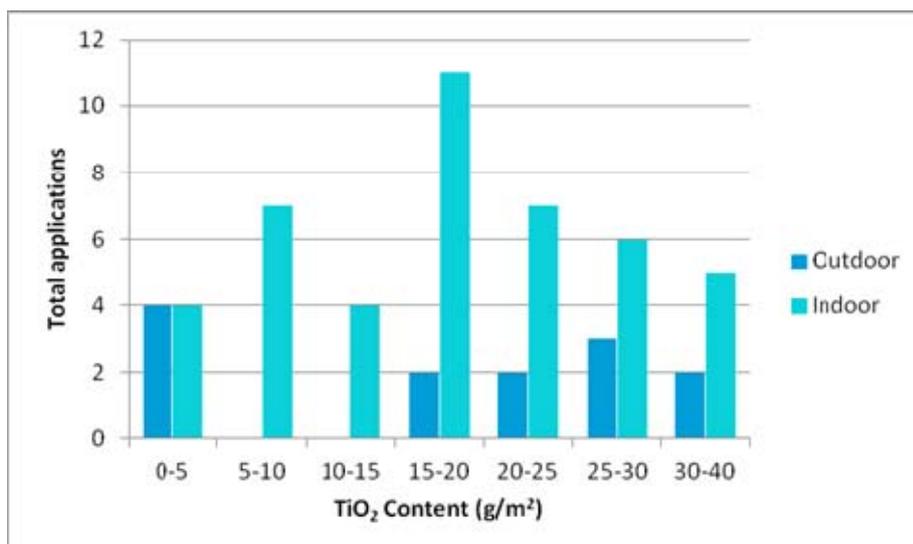


Figure 1: TiO₂ content in EU Ecolabelled paints

Based on this data, an opportunity exists to reduce the white pigment content of paints without excluding the majority of current EU Ecolabelled paints, however, comments from stakeholders suggested that a further reduction was not possible. At the 1st AHWG there was nearly a unanimous call to keep the levels as they are.

Stakeholders commented that elastomeric coatings, in particular PVC-based paints (A1-A5 according to EN 1062-1) and high binder content paints which are particularly used for high wet scrub resistance paints (class 1 in wet scrub resistance EN 13300), are currently excluded from the Ecolabel because of the current white pigment content requirements. These paints require more TiO₂ to achieve the requisite opacity. A 'second tier' white pigment limit has been proposed set specifically for high wet scrub resistant (Class 1) paints. Furthermore, there were several stakeholder submissions on including class 4 or 5 wet scrub resistant paints, particularly for matt paints. Class 4 wet scrub resistant paints could be used as the minimum performance benchmark. This would enable segregation between different grades of paint but also ensure that a minimum durability criterion is mandated. Three thresholds have been provided within the new criterion.

A competent body raised a concern that certain woodstains and varnishes contain small quantities of titanium dioxide. This led to the question about the need for these products to undergo spread-rate tests and the need to audit the emissions from titanium dioxide manufacture. This is confirmed by the data provided by competent bodies and collated under Figure 1, where a number of Ecolabelled paints have very low concentrations of TiO₂ (0-5 g/m²). This presents three issues:

1. Determining spread rates (if the paints are transparent) and, thus, the amount of TiO₂ per square meter may be very difficult.
2. Applicants will be required to perform additional analysis on products that will undoubtedly pass the current requirements.
3. TiO₂ which is produced using higher polluting routes can be used because the small amount of TiO₂ used in the paint formulation will mean that the total pollution levels for its production will be below the currently mandated threshold in criterion 2.

To mitigate against point 1, it could be proposed that a further explanation should be drafted into this criterion that describes which paints are exempted by using the exclusion clauses developed for criterion 7(a), namely varnishes, woodstains, floor coatings, floor paints, undercoats, adhesion primers or any other transparent coatings. This also addresses point 2.

To prevent the use of the approach described under point 3, modifying the calculation under criterion 2 to 'per gram of TiO₂', rather than 'per meter squared of paint' will ensure that low-polluting TiO₂ is used within the paint.

A suggestion was made to include weathering as a test for durability of the paint. Unfortunately, further information on how to integrate this system within the current testing requirements was not supplied. It is recommended that the use of weathering as a proxy for durability is re-examined at the next revision.

White pigment content (white inorganic pigments with a refractive index higher than 1,8): Paints shall have a white pigment content lower or equal to that described in the table below per m² of dry film, with 98 % opacity.

Wet scrub resistance	Indoor limit (g/m ²)	Outdoor limit (g/m ²)
Class 1	40	42
Class 2	36	38
Class 4 (Matt paints)	25	27

This requirement does not apply to varnishes and woodstains.

Assessment and verification: The applicant shall either provide a declaration of non-use or provide documentation showing the content of white pigments, the spreading rate and the assessment and verification criteria set out for the wet scrub resistance criterion, together with the detailed calculation showing compliance with this criterion.

3.1.2 Titanium Dioxide

As is described within the background report, titanium dioxide is a significant contributor to the environmental impact of paint. It is important in enhancing the performance of the paint and so a careful balanced approach is needed in order to ensure that high quality paints are produced, whilst minimising the impact to the environment. Within the current revision of the EU Ecolabel criteria on paints and varnishes, there is a criterion that limits the emissions from titanium dioxide production.

There is some dispute as to whether the intention of this criterion was to set limits on SO_x emissions and sulphate wastes from the chloride process. The Titanium Dioxide Harmonisation Directive³ does not stipulate limits for SO_x emissions for chloride wastes. Furthermore, stakeholders have argued that the levels of SO_x emissions from the chloride process are so low they can be excluded from the calculation. From data supplied by the Reference Document on Best Available Technology for the Manufacture of Large Volume Inorganic Chemicals (BREF) (August 2007), sulphur dioxide emissions are released (albeit to a lesser extent) during production of titanium dioxide via the chloride route. Table 3 shows SO_x emission from the production of TiO₂ via the chloride route and also calculates the effect of SO_x emissions on a typical paint formulation with a maximum of 38g of TiO₂ per square meter as mandated by criterion 1 for outdoor paints.

³ 92/112/EEC

Table 3: Emissions from European TiO₂ manufacturing plants using the chloride process based on BREF data⁴

SOx emissions from a chloride plant ⁵	SOx emissions per tonne of TiO ₂
Average	1.28 kg/tonne
Maximum	4.14 kg/tonne
Minimum	0.15 kg/tonne
SOx emissions per 38g of paint (based on BREF)	SOx emissions per m ²
Average	48 mg/m ²
Maximum	157mg/m ²
Minimum	5mg/m ²

Based on the argument provided above, the maximum amount of SOx emitted from a chloride based TiO₂ plant is 40% less than the threshold for the EU Ecolabel. Although the BREF report was published in 2007, the calculations within the report are based on data from 1999 and are out of date. Several stakeholders have stated that the SOx emissions from chloride plants are significantly lower than that provided by the sulphate route and therefore need not be included. Also, the Titanium Dioxide Harmonisation Directive does not require chloride route manufacturers to report SOx emissions making it difficult for these producers to provide evidence to the Ecolabel. This will have two possible consequences, either adding undue burden in monitoring and providing emissions data or effectively banning chloride-derived TiO₂ from the Ecolabel. As a result, it is proposed that SOx emissions should only be relevant to the sulphate route.

During the assessment process, an applicant stated that their TiO₂ supplier recycled their sulphur solid waste internally. Under such circumstances, the applicant argued that the sulphur should be considered a 'by-product' and exempt from the criterion. The Waste Framework Directive 2008/98/EC, article 3 defines waste: if this TiO₂ producer can satisfy article 5 (by-product production) of the Waste Framework Directive, then the sulphur waste can be exempt. A suggested amendment to the criteria has been made.

An analysis of anonymised data, received from successful EU Ecolabel applications from several National Competent Bodies, enabled a comparison of thresholds attained by submitted paint formulations. Table 4 summarises these results.

Table 4: Average emissions from the manufacture of TiO₂ for successful EU Ecolabel paint applications.

TiO ₂ Origin	Number of products	Average values per paint				
		SOx	S	Nat	Synth	Slag
Sulphate only processes	36	139	8.8			
(Standard Deviation)		56	4.2			
Chloride only processes	7			1.79	2.48	5.04
(Standard Deviation)				0.68	1.56	2.35
Mixed processes	38	99.4	7.3	1.83	3.17	5.66
(Standard Deviation)		87.9	5.7	1.04	1.79	3.54
Ecolabel limits (indoor)		252	18	3.7	6.4	11.9

⁴ Best Available Technology for the Manufacture of Large Volume Inorganic Chemicals (BREF), EC, August 2007

⁵ The figure takes into account the chlorination process and the energy to generate heat for the process.

If the product contains more than 3.0 weight % of titanium dioxide, the emissions and discharges of wastes from the production of any titanium dioxide pigment used shall not exceed the following (as derived from the Reference Document on Best Available Technology for the Manufacture of Large Volume Inorganic Chemicals (BREF) (August 2007)):

The sulphate process:

- SO_x calculated as SO₂: 7.0 kg/ton TiO₂
- Sulphate waste: 500 kg/ton TiO₂.

The chloride process:

- If natural ore is used, 103 kg chloride waste/ton TiO₂
- If synthetic ore is used: 179 kg chloride waste /ton TiO₂
- If rutile ore is used: 329 kg chloride waste /ton TiO₂.

If more than one type of ore is used, the values will apply in proportion to the quantity of the individual ore types used.

Note:

SO_x emissions only apply to the sulphate process.

For the avoidance of doubt, the Waste Framework Directive 2008/98/EC, article 3 defines waste. If the TiO₂ producer can satisfy article 5 (by-product production) of the Waste Framework Directive for its solid wastes then, the wastes shall be exempt.

Assessment and verification: The applicant shall either provide a declaration of non-use or provide the supporting documentation indicating the respective levels of emissions and discharges of wastes for these parameters, the titanium dioxide content of the product, the spreading rate, together with the detailed calculations showing compliance with this criterion.

4 Use

4.1 Efficiency in use

There have been several requests to provide guidance on the application of the "efficiency in use" criteria by stakeholders. A new criterion note is proposed below.

Dependant on the claims made on the properties of the paint, the following tests shall be undertaken.

Criteria	All	Outdoor ¹	Varnish	Floor covering and paint	Undercoat	Masonry paint
Spreading rate	X					
Wet scrub resistance	X					
Resistance to water			X			
Adhesion				X	X	X
Abrasion				X		X
Weathering		X				X
Water vapour permeability ²						X
Liquid water permeability ²						X
Fungal resistance ²						X
Crack bridging ²						X
Alkali resistance ²						X

Notes:

1 These are all products marketed as outdoor paints and include masonry paints

2 Only required where marketing claims are made about the paints

4.1.1 Spreading rate

A key environmental consideration is the amount of paint used during application. Minimising the amount of paint used, whilst achieving a high quality finish can result in a significant environmental saving. The most appropriate criterion by which this can be monitored is through the paints spreading rate. This is a criterion in the current revision of the EU Ecolabel Paints and Varnishes.

The interplay between this criterion and criterion 1 in section 3.1.1 mean that a variation in either has an impact on both. It is suggested that this criterion remains largely unchanged and that improvement in environmental performance should focus on the amount of white pigment within the formulations described in Section 3.1.1.

The test protocols defined within the cited standards have not been modified since the previous revision and can be used for the updated criteria document.

The performance criterion (spreading rate) for thick decorative coatings is missing for outdoor paints even though they are mentioned in the scope of the document. Most stakeholders suggest that the indoor criteria

can be also applied to outdoor products. Several stakeholders questioned the availability of appropriate thick decorative coatings for outdoor use, suggesting that any requirement would be redundant; however, several examples seem to be available.⁶ A combination of indoor and outdoor paint criteria may enable a unified threshold based on the current indoor level.

For opaque paints based on non-white (low TiO₂) bases, a gap currently exists in the ability to test their spreading rates. A possible option is the French test standard NF T30-073:1989-08-01, although the standard's popularity and use is unknown. Although information was sought, no additional information was forthcoming on the applicability or use of this standard, therefore it is suggested that it is not included within this revision.

A suggestion was made to differentiate the set limits for primers and undercoats. The reasoning behind is that the main function of a primer is to prepare the medium and to homogenize the porosity of the medium in order to give to the final coat a best adhesion. The adhesion is moreover proved by the test reports which should be made on the undercoats. Therefore it was argued that for primers and undercoats the focus should be on the limits for adhesion rather than spreading rate; the current ones are difficult to achieve. Further information and feedback from stakeholder to supportive this is needed before primers and undercoats should be treated separately. As the proposed limits are already in use and in the 1st AHWG there was no discussion on this point it is preliminary recommended to remain with the current proposal and to re-examine this at a later stage based on stakeholder response.

It is suggested that the term 'undercoat' is removed from the exempted list to align this criterion with the definition of undercoats and primers described in Section 2.3.

White paints and light-coloured paints (including finishes, primers, undercoats and/or intermediates) shall have a spreading rate (at a hiding power of 98 %) of at least 8m² per litre of product for indoor paints and 6m² for outdoor paints. For tinting systems, this criterion applies only to the white base (the base containing the most TiO₂). In cases where the white base is unable to achieve this requirement, the criterion shall be met after tinting the white base to produce the standard colour RAL 9010.

For all other bases used to produce tinted products — these are bases which as a rule contain less TiO₂, which are unable to achieve the requirement of at least 8m² per litre of product at a hiding power of 98 % — the criterion shall not apply. For paints that are a part of a tinting system, the applicant must advise the end-user on the product packaging and/or POS which shade or primer/undercoat (if possible bearing the Community Eco-label) should be used as a basecoat before applying the darker shade.

Primers with specific blocking/sealing, penetrating/binding properties and primers with special adhesion properties for aluminium and galvanised surfaces shall have a spreading rate (at a hiding power of 98 %) of at least 6m² per litre of product.

Thick decorative coatings (paints that are specially designed to give a three-dimensional decorative effect and are therefore characterised by a very thick coat) shall alternatively have a spreading power of 1m² per kg of product.

Elastomeric paints shall have a spreading rate (at a hiding power of 98 %) of at least 4m² per litre of product.

This requirement does not apply to varnishes, woodstains, floor coatings, floor paints, primers or any other transparent coatings.

Assessment and verification: The applicant shall provide a test report using the method ISO 6504/1 (Paints and varnishes — determination of hiding power — Part 1: Kubelka-Munk method for white and light-coloured paints) or 6504/3 (Part 3: determination of contrast ratio (opacity) of light-coloured paints

⁶ <http://www.rialto-colors.com/wall-coatings/thick-coatings.asp>

at a fixed spreading rate), or for paints specially designed to give a three-dimensional decorative effect and characterised by a very thick coat the method NF T 30 073 (or equivalent). For bases used to produce tinted products not evaluated according to the abovementioned requirements, the applicant shall produce evidence of how the end-user will be advised to use a primer and/or grey (or other relevant shade) of undercoat before application of the product.

4.1.2 Wet scrub resistance

Wet scrub resistance can be considered a means to determine the durability of a particular paint. Manufacturers state that this is one of the key performance indicators for hard wearing paints (particularly floor and bathroom/kitchen paint). The durability of a paint is important in reducing its environmental impact. As is shown within the LCA in the background report, any increase in time between repaints, in this case due to an increase in wear resistance, leads to a decrease in the overall lifecycle impact of the paint.

A lengthy debate over the inclusion and scale of this requirement preceded the development of the current criterion. A key concern is whether this test needs to be carried out for all paints or only for those claiming wet scrub resistance. From an environmental perspective, more durable paints would reduce the environmental impact by increasing intervals between repainting. This was particularly addressed in the technical analysis⁷. However, the proposed universal requirement that all paints must meet this target was opposed because it would exclude most matt wall paints and was seen as unnecessary for wood and trim paints. Consensus on these issues has yet to be reached, with both views expressed within the stakeholder consultation; therefore, any proposed changes would need further stakeholder engagement and agreement prior to a final decision.

The significant environmental impact of improving the durability of the paint means that increasing the wet scrub resistance test is desirable. The additional positive consequence is that Ecolabel paints would be perceived to be high performance paints. It is proposed within the wet scrub resistance criterion that there is gradation of maximum concentrations of white pigment within the paint. This will allow higher quality paints to undergo Ecolabelling. To complement this, a change to this criterion is needed. A possible suggested solution is that the scrub resistance test should be 'graded' to enable differentiation between brushable (class 2) and washable (class 1) paints. This could be extended to class 4 paints as well (matt paints). As a result, all paints will need to undergo wet scrub resistance testing. This would add an additional cost burden to the paint manufacturers but will significantly improve the quality of Ecolabelled paint.

A small change has been requested from the stakeholders that "class 2 or better" means ≤ 2 . The currently specified test protocols are up to date and appropriate for determining wet scrub resistance. The text has been changed to reflect this point.

⁷ <http://susproc.jrc.ec.europa.eu/paints/stakeholders.html>

All paints shall have a wet scrub resistance as measured by EN 13300 and EN ISO 11998 of class 4 (not exceeding 70 microns after 200 cycles).

Paints (according to EN 13300) for which claims are made (whether on the product or in related marketing material) that they are brushable, shall have a wet scrub resistance as measured by EN 13300 and EN ISO 11998 of class 2 (not exceeding 20 microns after 200 cycles).

Paints (according to EN 13300) for which claims are made (whether on the product or in related marketing material) that they are hard wearing, shall have a wet scrub resistance as measured by EN 13300 and EN ISO 11998 of class 1 (not exceeding 5 microns after 200 cycles).

Due to the large potential range of possible tinting colours, this criterion will be restricted to the testing of tinting bases.

Assessment and verification: The applicant shall provide a test report according to EN 13300 using the method EN ISO 11998 (Test for cleanability and scrub resistance).

4.1.3 Resistance to water

This test is important for water resistant paints. The current test protocol is the latest available version. However, an international review of the ISO standard is under way and a document has been circulated through the technical committee for comment. The publication date of the new standard is unknown but is likely to occur during the lifetime of the new criteria document; therefore, the wording within the criterion must reflect this anticipated change.

There was also a request to clarify that all varnishes, not just floor varnishes, shall meet this criterion.

Recommended minor amendments to the criterion text are suggested below.

All varnishes, floor coatings and floor paints shall have a resistance to water, as determined by ISO 2812-3 such that after 24 hours' exposure and 16 hours' recovery no change of gloss or of colour occurs.

Assessment and verification: The applicant shall provide a test report using the method ISO 2812-3 (Paints and varnishes — determination of resistance to liquids — Part 3: Method using an absorbent medium).*

*This test procedure is due for revision during the lifetime of this criterion. If there is a substantive change to this procedure, a decision by the Competent Body Forum shall be taken on the appropriate test standard used.

4.1.4 Adhesion

The protocol has not been updated since the previous revision of the Ecolabel and there is consensus that this is appropriate for continued use in the EU Ecolabel. It is recommended that the test should be reused without revision. Stakeholders agreed on this in the 1st AHWG.

Pigmented masonry primers shall score a pass in the EN 24624 (ISO 4624) pull-off test where the cohesive strength of the substrate is less than the adhesive strength of the paint, otherwise the adhesion of the paint must be in excess of a pass value of 1,5MPa.

Floor coatings, floor paints, floor undercoats, metal undercoats and wood undercoats shall score ≤ 2 in the EN 2409 test for adhesion. Transparent primers are not included in this requirement

The applicant shall evaluate the primer and/or finish alone or both as part of a system [the system when tested shall concern products if possible labelled with the European Ecolabel (with the exception of systems designed for metal surfaces)]. When testing the finish alone, this shall be considered the worst case scenario concerning adhesion.

Assessment and verification: The applicant shall provide a test report using the method EN ISO 2409 or EN 24624 (ISO 4624) as applicable.

4.1.5 Abrasion

The protocol has not been updated since the previous revision of the Ecolabel and there is consensus that this is appropriate for continued use in the EU Ecolabel.

Floor coatings and floor paints shall have an abrasion resistance not exceeding 70 mg weight loss after 1000 test cycles with a 1000 g load and a CS10 wheel according to EN ISO 7784-2:2006.

Assessment and verification: The applicant shall provide a test report showing compliance with this criterion using the method EN ISO 7784-2:2006.

4.1.6 Weathering

An appropriate colour change test was not stipulated within the current criterion. The use of ISO 7724-3:1984 was suggested as the most appropriate standard available, which achieved general agreement from the stakeholders. This standard is due to be superseded by ISO 11664 within the timeframe of the next revision of the EU Ecolabel criteria document. This must be taken into account when drafting the new criterion. Appropriate wording has been provided on this point.

All other test specifications cited within this document are up-to-date and appear suited for their respective identified roles and will be used as in the criterion.

The current criterion does not account for possible colour changes in transparent, coloured products such as woodstains. This is a problem because the substrate has an impact on the overall colour of the paint and any colour change to the wood substrate due to weathering will affect the results of a test. A temporary solution proposed by the Competent Body Forum was the use of an inert substrate such as glass or metal to remove the effect of the wood on the overall test results. This proposal has met with significant resistance: it is argued that using an artificial substrate will have an impact on the performance of the woodstain. In particular, the adhesion and flaking properties of the paint will be significantly affected. This in turn is likely to have an impact on the performance of the colour fade of the paint.

It seems clear that testing the adhesion characteristics of the paint should be conducted on the appropriate substrate (in the case of woodstains, on untreated wood). There is a further question as to whether an additional separate test on an inert material could be used to measure colour change due to weathering. An appropriate white primer could be used to enhance adhesion of the woodstain to the inert substrate. Some stakeholders are concerned, however, that the higher financial costs associated with the additional tests would be prohibitive.

Additional stakeholder feedback was not received on this issue from the 1st AHWG, therefore no additional clause will be added in this revision, with a recommendation that the issue is revisited at the next revision.

A minor change to the text is required to state that the gloss finishing tests only apply to gloss and satin paints and varnishes and they are inappropriate for matt paints. Appropriate text has been suggested.

Masonry finish paints and wood and metal finishes including varnishes shall be exposed to artificial weathering in apparatus including fluorescent UV lamps and condensation or water spray according to 11507:2007.

Masonry paints shall be exposed to test conditions for 1 000 hours, wood and metal finishes (including varnishes) shall be exposed to test conditions for 500 hours. Test conditions are: UVA 4h/60degC + humidity 4h/50degC.

Alternatively, wood finishes and wood varnishes may be exposed to weathering for 500 hours in the QUV accelerated weathering apparatus with cyclic exposure with UV(A) radiation and spraying according to EN 927-6.

According to ISO 7724-3:1984, the colour change of samples exposed to weathering shall not be greater than $\Delta E^* = 4$ and is not applicable to transparent varnishes and bases. To determine colour change of woodstains, a separate sample shall be prepared using an inert substrate and undergo weathering using a standard protocol outlined above.

Decrease samples in gloss for paints and varnishes exposed to weathering shall not be greater than 30 % of its initial value and shall be measured using ISO 2813. This is not applicable to matt-finish paints.

Chalking shall be tested using method EN ISO 4628-6:2007 on masonry finish coats and wood and metal finishes (where applicable) after the samples have been exposed to weathering. Coatings shall achieve a score of 1,5 or better (0,5 or 1,0) in this test. In the standard there are illustrated references.

The following parameters shall also be evaluated on masonry finish coats and wood and metal finishes after the samples have been exposed to weathering:

- Flaking according to ISO 4628-5:2003; flake density 2 or less, flake size 2 or less
- Cracking according to ISO 4628-4:2003; crack quantity 2 or less, crack size 3 or less
- Blistering according to ISO 4628-2:2003; blister density 3 or less, blister size 3 or less.

Due to the large number of possible tinting colours, these tests will be restricted to the base paint used.

Assessment and verification: The applicant shall provide test reports using either ISO11507:2007 according to the specified parameters or EN 927-6, or both (if relevant). The applicant shall provide test reports using EN ISO 4628-2, 4, 5, 6 where applicable. **Additionally, the applicant shall provide a test report in conformance to ISO 7724-3:1984* (where applicable).**

*This test procedure is due to be superseded by ISO 11664 during the lifetime of this criteria. If substantial changes to this procedure have been made, a decision by the Competent Body Forum shall be taken on the appropriate test standard to be used.

4.1.7 Water vapour permeability

The protocol has not been updated since the previous revision of the Ecolabel and there is consensus that this is appropriate for continued use in the EU Ecolabel. This criterion will be included without revision.

Where claims are made that exterior masonry and concrete paints are breathable the paint shall be classified as class II (medium vapour permeability) or better according to the test method EN ISO 7783-2. Due to the large number of potential tinting colours, this criterion will be restricted to testing of the base paint; this requirement is not applicable to transparent primers.

Assessment and verification: The applicant shall provide a test report using methodology EN ISO 7783-2.

4.1.8 Liquid water permeability

The test protocol has not been updated since the previous revision of the Ecolabel and there is consensus that this is appropriate for continued use in the EU Ecolabel. A minor change made is removing the "DIN" identifier of the standard.

Where claims are made that exterior masonry and concrete paints are water repellent or elastomeric, the coating shall be classified as class III (low liquid permeability) according to method EN 1062- 3:1999. Due to the large number of potential tinting colours, this criterion will be restricted to the testing of the base paint. All other masonry paints shall be classified as class II (medium liquid permeability) or better according to the test method EN 1062-3:1999.

Assessment and verification: The applicant shall provide a test report using methodology EN 1062-3:1999.

4.1.9 Fungal resistance

The protocol has not been updated since the previous revision of the Ecolabel and there is consensus that this is appropriate for continued use in the EU Ecolabel. This criterion will be included without revision.

Where claims are made that masonry finish coatings have anti-fungal properties, the coating shall have a score of 2 or better (less than 10 % fungal coverage), as determined by method BS 3900:G6. Due to the large number of possible tinting colours, this criterion will be restricted to the testing of the base paint.

Assessment and verification: The applicant shall provide a test report using methodology BS 3900:G6.

4.1.10 Crack bridging

The test protocol has not been updated since the previous revision of the Ecolabel and there is consensus that this is appropriate for continued use in the EU Ecolabel. A minor revision made is removing the "DIN" identifier of the standard.

Where claims are made that masonry (or concrete) paint has elastomeric properties, it shall be at least classified as A1 at 23 °C according to EN 1062-7:2004. Due to the large number of potential tinting colours, this criterion will be restricted to the testing of the base paint.

Assessment and verification: The applicant shall provide a test report using methodology DIN EN 1062-7:2004

4.1.11 Alkali resistance

The protocol has not been updated since the previous revision of the Ecolabel and there is consensus that this is appropriate for continued use in the EU Ecolabel. This criterion will be included without revision.

Masonry paints and primers shall show no noticeable damage when the coating is spotted for 24 hours with 10 % NaOH solution according to method ISO 2812-4:2007. The evaluation is done after 24 hours drying-recovery.

Assessment and verification: The applicant shall provide a test report using methodology ISO 2812-4:2007.

4.1.12 Corrosion resistance

The inclusion of anti-corrosion paints would mandate an additional performance criterion. Further input from stakeholders is needed to draft this criterion. As reference basis is proposed EN ISO 12944 – part 6 referring to class C3 – (low/rural) with medium durability. Furthermore, for the measurement method could be used ISO 4628 for -2 blistering and -3 rusting.

4.2 Emissions during use

4.2.1 Volatile organic compounds

Volatile Organic Compounds (VOCs) are used as solvents within paints to help keep it stable prior to use and aid in spreading and delivery of the paint to the substrate. VOCs encompass a wide variety of compounds and are generally classed as organic substances with a boiling point less than 250 °C.⁸ VOCs generally evaporate or sublime from the paint during and after application. The release of these emissions can cause eye, nose, and throat irritation along with headaches and loss of coordination. Due to the wide diversity of compounds encompassed by this classification, more extreme reactions can also present, in particular: damage to liver, kidney, and central nervous system and some are suspected or known to cause cancer in humans.⁹

The current VOC limits within the EU Ecolabel criteria are based on modified (reduced) 2010 limits from the Paints Directive 2004/42/EC. A recast of the Directive is underway but no change on the limits is proposed.¹⁰ Therefore, further amendments to the Ecolabel thresholds will go beyond the values proposed within the Paints Directive.

Table 5 compares the VOC Directive's more stringent 2010 criteria with those stipulated within the EU Ecolabel Paints and Varnishes criteria (both for indoor and outdoor paints). As can be seen, the level set within the EU Ecolabel criteria ranges between 0 and 55% lower than the corresponding restrictions mandated within the

⁸ Directive 2004/42/CE

⁹ <http://www.epa.gov/iaq/voc.html>

¹⁰ http://ec.europa.eu/environment/air/pollutants/stationary/paints/paints_review.htm

VOC Directive. Feedback from the stakeholders stated that further reductions in certain product groups may be possible. The suggested reductions have been included in the final column of the table.

Table 5: Comparison between the VOC Directive emission limits, those mandated in the EU Ecolabel and stakeholder feedback on achievable levels.

Class	Description	Current levels	EU Ecolabel	% difference	Stakeholder feedback
A	Interior matt walls and ceilings (Gloss <25@60°)	30	15	50	10
B	Interior glossy walls and ceilings (Gloss >25@60°)	100	60	40	35-50
C	Exterior walls of mineral substrate	40	40	0	30-25
D	Interior/exterior trim and cladding paints for wood and metal	130	90	30.7	90-60
E	Interior/exterior trim varnishes and woodstains, including opaque woodstains	130	75 indoor 90 outdoor	42.3 30.7	50-90 60-90
F	Interior and exterior minimal build woodstains	130	75	42.3	40-55
G	Primers	30	15	50	10-15
H	Binding primers	30	15	50	10-15
I	One-pack performance coatings	140	100	28.6	60-100
J	Two-pack reactive performance coatings for specific end use such as floors	140	100	28.6	60-100
L	Decorative effect coatings	200	90	55	65-90

Data gathered from dossiers of successful EU Ecolabel applications have been provided as anonymised data from the Competent Bodies and summarised in Table 6.

Table 6: A summary of the VOC levels of EU Ecolabelled paints and varnishes

Type	Competent body data			Criteria maximum	Difference	% difference
	Average	Standard deviation	No. of licenses			
1 Pack performance coatings	77.8	21.6	8	100	22.2	22.2
Exterior trim and cladding paints for wood and metal including undercoats	41.2	2.7	10	90	48.8	54.2
Exterior trim varnishes and woodstains, including opaque woodstains	12.0	7.9	23	90	78.0	86.7
Interior Matt (walls/ceiling) (Gloss < 25@60 °)	2.9	3.4	60	15	12.1	80.7
Interior minimum build woodstains	42.5	14.8	6	75	32.5	43.3
Interior trim and cladding paints for wood and metal including undercoats	70.9	18.3	16	90	19.1	21.2
Interior trim varnishes and woodstains, including opaque woodstains	46.9	23.8	35	75	28.2	37.5
Primers (indoor)	5.0	0.0	2	15	10.0	66.7

A full analysis of the list is not possible on all paint types due to a lack of data for certain paint-types. Additional information from stakeholders is requested. Where data is available, though, the average VOC content of EU Ecolabelled products is significantly lower than the Criterion threshold for the paint (except for interior glossy and primers – where only one submission has been recorded and meaningful results are not possible to derive).

Based on the evidence above, examining the stakeholder feedback, other ecolabelling schemes, analysis of dossiers from competent bodies and a desire to improve standards, Table 7 provides new EU Ecolabel limits for VOC content in paint.

Table 7: Proposed changes to the VOC levels for Ecolabelled paints

Description	EU Ecolabel (g/l)	New limits
Interior matt walls and ceilings (Gloss <25@60°)	15	10
Interior glossy walls and ceilings (Gloss >25@60°)	60	40
Exterior walls of mineral substrate	40	25
Interior/external trim and cladding paints for wood and metal	90	80
Interior/external trim varnishes and woodstains, including opaque woodstains	75 indoor 90 outdoor	65
Interior and exterior minimal build woodstains	75	75
Primers	15	10
Binding primers	15	10
One-pack performance coatings	100	50
Two-pack reactive performance coatings for specific end use such as floors	100	80
Decorative effect coatings	90	80

Stakeholders request that the calculation for the VOC limits should apply to paint in a ‘ready-to-use’ state rather than ‘in can’. This will prevent the addition of extra solvent to the paint prior to use, which could have adverse effect on the user. Recommended wording has been added to the new criterion.

The decline in use of VOCs has led to an increase in the use of Semi Volatile Organic Compounds (SVOC’s). SVOCs, found in adhesives for floors and wall covering materials, are defined as having a boiling point of 380-400°C. To a certain extent, the restrictions on SVOCs have been covered by VAH’s and phthalates. Both the Austrian Ecolabel¹¹ and the German Blau Engel (Blue Angel)¹² specifically limit their use in paints, so inclusion in the EU Ecolabel will harmonise criteria.

Construction and building products are a major source of SVOCs and the Construction Products Directive¹³ has an optional criterion¹⁴ that SVOCs need to be avoided within the sector¹⁵. The major issue is that SVOC’s can

¹¹ Austrian Ecolabel UZ01 (2010)

¹² Blau Engel RAL UZ 12a

¹³ Construction products directive 89/106/EEC

¹⁴ European Collaborative Action. Urban air, indoor environment and human exposure. Report No 27; Harmonisation framework for indoor material labelling schemes in the EU (2010)

¹⁵ CEN/TC 351 Construction products: Assessment of the release of dangerous substances.

redistribute themselves from one surface, such as paints, onto other surfaces, from which they can be inhaled and ingested.¹⁶

It is recommended that an additional clause is added to this criterion based on values provided by alternative Ecolabels. Input from stakeholders is sought as to the level of restriction. Feedback on the inclusion or range for SVOC was not provided by stakeholders. It is suggested that the Austrian Ecolabel threshold of 3% (30 g/l) is used.

The compounds: 2 butoxyethyl acetate, diethylene glycol methyl ether, ethylene glycol, triethylene glycol are prohibited from Austrian Ecolabel - Paints, Varnishes and wood sealant lacquers UZ01 (2010) and diethylene glycol methyl ether, ethylene glycol, triethylene glycol are prohibited under the Austrian Ecolabel - Wall paints UZ17 (2010). The hazardous nature of these compounds means that they are explicitly prohibited from use under the new hazardous substances criteria set out in Section 4.2.10. As a result, additional criterion is not needed.

A further threshold is suggested for anti-corrosion paints.

Volatile Organic Compounds (VOC) shall not exceed:

Description	VOC limits (g/l including water)
Indoor matt walls and ceilings (Gloss <25@60°)	10
Indoor glossy walls and ceilings (Gloss >25@60°)	40
Outdoor walls of mineral substrate	25
Indoor/Outdoor trim and cladding paints for wood and metal	80
Indoor trim varnishes and woodstains, including opaque woodstains	65
Outdoor trim varnishes and woodstains, including opaque woodstains	75
Indoor and Outdoor minimal build woodstains	50
Primers	10
Binding primers	10
One-pack performance coatings	80
Two-pack reactive performance coatings for specific end use such as floors	80
Decorative effect coatings	80
Anti-corrosion paints	80

In this context volatile organic compounds (VOC) means any organic compounds having an initial boiling point less than or equal to 250°C measured at a standard pressure of 101,3 kPa as defined in Directive

¹⁶ EnVIE; Coordination Action on Indoor air Quality and Health Effects

2004/42/EC. The subcategories for paints and varnishes of the Directive are used for defining VOC limits. **These values shall be measured at the point of application and must include any additional solvent added to the paint prior to application.**

The total Semi Volatile Organic Compound (SVOC) shall be limited to 30 g/l including water. SVOC are defined as organic substances or mixtures with a boiling range between 250 and 400°C.

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion. For all products the applicant shall indicate the VOC and SVOC content.

4.2.2 Indoor air quality

Studies in the 1980's in the USA¹⁷ showed that the contamination of indoor air by 12 of the most commonly encountered organic pollutants (VOCs) was between 2 and 5 times that found in outside air irrespective of whether it was in a rural or industrial environment. Limiting emissions to air will reduce health impacts from exposure to VOCs.

The background report described the desire as well as the trend toward Indoor Air Quality (IAQ) testing. Although this is a nascent subject, requirements in Germany and, in particular, France are suitable for inclusion into the EU Ecolabel. In general, there is support for the use of IAQ to determine the emissions of VOC from paint. However, stakeholders are concerned over the cost as well as the fact that an international test has yet to be agreed. These concerns are real and have been taken into account. The trend towards IAQ testing cannot be ignored through the EU Ecolabel, therefore the following criterion is proposed (based upon the French criterion).

Indoor Air Quality

Each indoor paint shall undergo testing for indoor air quality and meet Class A+ as defined within French Decree NOR : DEVL1104875A. This requirement is restricted to the lightest colour paint within a series or, in tinting systems, the base paint.

Verification and assessment: The applicant shall provide test results using the methodology described within NOR: DEVL1104875A.

4.2.3 Metals

In large quantities, certain metals are considered carcinogenic and hazardous to human health¹⁸. Although present in the environment, and necessary for human health in small amounts, any large concentration can cause acute or chronic toxicity¹⁹. As they are elements, they cannot be broken down and therefore will persist in the environment²⁰. When absorbed by humans, they have been shown to have detrimental effects on kidney function, reproductive organs and the nervous system, particularly in unborn infants and young children.

It is unclear from the current wording if the amount of allowable trace concentrations of these compounds is the sum of all eight or applies to each individual one. Information provided from minutes of the previous revision of the EU Ecolabel criteria suggest that the intention was that the 0.01% (m/m) threshold was per

¹⁷ EPA's Office of Research and Development's "Total Exposure Assessment Methodology (TEAM) Study" (Volumes I through IV, completed in 1985

¹⁸ http://www.apis.ac.uk/overview/pollutants/overview_HM.htm

¹⁹ <http://www.lef.org/protocols/prtcl-156.shtml>

²⁰ http://www.apis.ac.uk/overview/pollutants/overview_HM.htm

metal. Also, clearer wording was suggested and agreed for the derogations surrounding cobalt by the CB working group.

Appropriate wording has been provided to clarify that this criterion is focused on a per metal basis and the agreed wording change has been made.

A further reduction in trace quantities of metal appear to be impractical at this stage.

Through stakeholder engagement, the clause that permits the use of barium sulphate has been questioned. Several other insoluble barium compounds may be present within certain mineral fillers and the inclusion of barium sulphate over these barium containing compounds appears to be arbitrary. Similarly, some have requested antimony in insoluble TiO₂ lattices to be exempt from this criterion on the basis that they are essentially non-toxic. Further submissions on this topic were not provided by stakeholders and therefore an amendment will not be made. It is recommended that this subject is re-visited at the next criteria revision.

Concerns have been raised that the current verification and assessment methods - SDS analysis and supplier declarations - are inappropriate to determine the metal content of the paints. A shift in the assessment has been proposed from analysis of the ingredients to analysis of the amount of metal available for release to the environment in the final product. A recently developed test protocol: EN 71-3, which examines the metal content in toys, could be an alternative. There was some support for the use of this test, however, several stakeholders questioned its applicability to the Ecolabel. One concern was that each tinting system may need a separate test which would be prohibitively expensive. There are also concerns that, being designed for toys, the test is not fit for purpose. In conclusion, there does not appear to be consensus over the use of an alternative testing regimen for determining the amount of metal in the paint.

The derogation for cobalt siccatives within this criterion overlaps with that presented within Section 4.2.10, Hazardous Substances. Phrasing has been suggested within this criterion and an appropriate derogation has been suggested within the Hazardous Substances criterion. Stakeholders have not provided any derogation requests for cobalt pigments. If there is a need for the use of cobalt pigments, a derogation under the Hazardous Substances criteria will be needed. However, if alternatives are widely available, the need for a derogation should be reconsidered.

The following metals or their compounds shall not be used as an ingredient of the product or tint (if applicable) (whether as a substance or as part of any preparation used): cadmium, lead, chromium VI, mercury, arsenic, barium (excluding barium sulphate), selenium, antimony **and cobalt**.

It is accepted that ingredients may contain traces of these metals up to **0.01** deriving from impurities in the raw materials **and can be present at these quantities for each metal for each ingredient**.

Derogations for substances containing cobalt are described under the Hazardous Substances criterion.

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion as well as declarations from ingredient suppliers (where applicable).

4.2.4 Volatile Aromatic Hydrocarbons

VAHs have specific environmental and human health impacts including DNA damage.²¹ Exposure to these products should be minimised and any way to mandate a reduction in their use encouraged. The current criterion prevents their addition, with all stakeholders reporting their approval but allows their presence from

²¹ Environ Health Perspect. 2002 June; 110(Suppl 3): 451-488.

impurities. A reduction in the amount of VAH present (from impurities) from 0.1 % (w/w) to 0.01% (w/w) as mandated in the Austrian Ecolabel in the final paint was explored.

A minimum threshold rather than a complete prohibition is important because VAHs are widely used monomers in production of binders for paints, particularly styrene in vinyllic emulsions. Under normal chemical synthesis, total conversion of styrene into a polymer is impossible and trace amounts of monomer will be present in the final product. Stakeholders have suggested that a further reduction of the threshold would be too strict for most of the low and medium PVC paints and that compliant with the requirements will be technically difficult. This is particularly acute for paints that contain a large amount of binder. Some stakeholders suggested that the reduction could be achieved but concerns surround enforceability: whether suitable analytical techniques are available to verify this level is unclear, as is the likelihood that paint manufacturers can provide the necessary information.

The response from industry stakeholders in the meeting was to remain at the current limit. However, a few Member States recommended an uptake of the Austrian Ecolabel limit of 0.01% though this recommendation was not substantiated with technical information and, due to the technical reasons outlined above, is unlikely to lead to further environmental gains.

The proposed criterion on hazardous substances outlined in Section **Error! Reference source not found.** covers this aspect. A derogation concerning mixtures of substances that contain VAHs will be made and this criterion removed. The relevant part of the hazardous substances criterion presented in Section 4.2.10 is as follows:

(Part of Hazardous Substances criterion)

USE	Chemical Composition Ingredient	CAS/ EINECS	Classification	Note
Unreacted impurity	Volatile Aromatic Hydrocarbons	Various	Various	7

Note:

7- Ingredients containing Volatile Aromatic Hydrocarbons may be added up to such a limit that the VAH content in the end product will not exceed 0,1 % (w/w). In this context volatile aromatic hydrocarbon (VAH) means any organic compound, as defined in Directive 2004/42/EC, having an initial boiling point less than or equal to 250°C measured at a standard pressure of 101,3 kPa and having at least one aromatic nucleus in its developed structural formula.

4.2.5 Alkylphenoxyethoxylates

APEOs are non-ionic surfactants, which have an emulsifying and dispersing effect when processing paints, and in binders, dispersion aids, thickeners, driers, anti-foam agents and pigment pastes.²² APEOs are produced in large volumes, with uses that lead to widespread release to the aquatic environment. They are highly toxic to aquatic organisms, and in the environment degrade to more environmentally persistent compounds. These chemicals have been detected in human breast milk, blood, and urine and are associated with reproductive and developmental effects in rodents.²³

This criterion overlaps with the new hazardous substances requirements described within Section 4.2.10 and therefore can be removed from the new EU Ecolabel criteria document.

²² Paints and how they affect the environment, Tommi Nurmi and Konsta Kannianen, 2008

²³ http://www.epa.gov/oppt/existingchemicals/pubs/actionplans/RIN2070-ZA09_NP-NPEs%20Action%20Plan_Final_2010-08-09.pdf

4.2.6 Isothiazolinone compounds

Isothiazolinone compounds are found in wood coatings²⁴ and in some paint formulations. They are a broad spectrum fungicide, algicide and bacteriostat used in solvent based coatings, surface protection products and other xylene compatible products.²⁵ For people susceptible to their effects, the compounds can cause irritation to the skin and mucous membranes.²⁶ The extent to which they have harmful effects depends greatly on the level of concentration in the product used and on the method of exposure – long-term oral exposure being particularly hazardous.²⁷

There was a wide consensus among stakeholders that isothiazolinone biocides are necessary both for preserving the products in the can, and for their properties as a preservative while the product is in use (particularly in outdoor use). While further reduction in the levels of these compounds is desirable, most stakeholders suggested that this was difficult and impractical due to the lack of a viable alternative.

A proposal was made to increase the coverage of this criterion to include Iodopropynyl butylcarbamate (IPBC) as an alternative preservative. It was argued that there were benefits of reduced environmental damage from its use. Further information from stakeholders was requested but was not provided. It is suggested that this issue is revisited at the next revision of the criteria.

This criterion overlaps and can be incorporated with the new hazardous substances requirements described within Section 4.2.10 through the drafting of an appropriate derogation. Several stakeholders have provided information on derogations for these materials. The following derogation is suggested for the inclusion under hazardous substances criterion:

(Part of Hazardous Substances criterion,

Note: the substances are presented as an example (non exhaustive list) s. also hazardous substances criterion)

USE	Chemical Composition Ingredient	CAS/ EINECS	Classification	Note
In can preservative	2-Methyl-2H-isothiazol-3-one	2682-20-4	R 22-23-34-43-50	1
	1,2-Benzisothiazol-3(2H)-one	2634-33-5	R 22-38-41-43-50	1
	Methyl-4-isothiazolin-3-one	2682-20-4	R34-37-43-50-24/25	1
	mixture of: 5-chloro-2-methyl-4-isothiazolin-3-one [EC no. 247-500-7] and 2-methyl-2H-isothiazol-3-one [EC no. 220-239-6] (3:1)	55965-84-9	R23/24/25-34-43-50-53	3
	mixture of: 5-chloro-2-methyl-4-isothiazolin-3-one [EC no. 247-500-7] and 2-methyl-2H-isothiazol-3-one [EC no. 220-239-6] (3:1)	55965-84-9	R23/24/25-34-43-50-53	3
Dry film preservative	2-Octyl-2H-isothiazol-3-one	26530-20-1	R 22, 23/24-34-43-50/53	1
	1,2-Benzisothiazolin-3-one	2634-33-5	R 22-38-41-43-50	1

Notes:

24 Revision of European Ecolabel and Development of Green Public Procurement Criteria for Indoor and Outdoor Paints and Varnishes, October 2011

25 Akcros Chemicals, <http://www.akcros.com/products/europeproductrange/productsbycategory/microbiocides.aspx>

26 Consumer exposure to biocides - identification of relevant sources and evaluation of possible health effects, Stefan Hahn, February 2010

27 Consumer exposure to biocides - identification of relevant sources and evaluation of possible health effects, Stefan Hahn, February 2010

¹The sum of the total allowable concentration of these compounds is 0.05 % (w/w) before or after tinting (if applicable).

².For outdoor wood coatings the total allowable concentration shall not exceed 0.2 % (w/w).

³.The sum of the total allowable concentration of these compounds is 0.0015 % (w/w).

4.2.7 Perfluorinated alkyl sulfonates (PFAS)

There was a stakeholder consensus that this criterion should remain unchanged. These compounds are hazardous and therefore overlap with the new hazardous substances requirements described within Section **Error! Reference source not found.**. This criterion will be removed from the new EU Ecolabel criteria document.

4.2.8 Halogenated Organic Solvents

Halogenated organic solvents can be found in paint thinners, strippers and solvents. They are largely non-flammable, though if they do combust, they can produce toxic gases. Risk to health from using halogenated organic solvents in paint includes dermatitis and eye irritation. More serious exposure via vapours or high levels of the solvents can lead to kidney and liver damage, heart irregularities and are potentially carcinogenic.²⁸

Comments from stakeholders have revealed an apparent confusion over the targeted compounds of this criterion, which is entitled 'Halogenated Organic Solvents', whereas the text describes 'Halogenated Organic Compounds'. These two groups of compounds differ significantly, and several stakeholders were concerned about a prohibition on the use of "halogenated compounds" since the latter are used in many pigment systems. Investigation of the original documentation provides no additional insight into the aim of this criterion but, due to the use of halogenated tinting systems, complete prohibition of all compounds is impossible.

There was a further request to increase the threshold of this requirement to include halogenated pigments by ensuring they meet the EU's requirements for colour pigments in food packages according to Resolution AP (89). There is little data on the performance effect of increasing the stringency of the requirements on pigments beyond the current thresholds. Even from a basic analysis, pigments on walls need to last significantly longer than on food packaging. Without further data on the ability of these pigments to achieve this performance level this additional requirement should be deferred until the next revision.

All hazardous halogenated compounds are now covered under the new Hazardous Substances Criterion in section **Error! Reference source not found.**. The separate Halogenated Organic Compounds criterion is now redundant and has been removed.

4.2.9 Biocides

The original EU Ecolabel criteria for both indoor and outdoor paints did not adequately control the inclusion and use of biocides in paints. The revision to the Biocide Directive and the recently developed EU Ecolabel criteria for other products that contain biocides should be examined within this revision.

In addition to the new criterion for other EU Ecolabel products, alternative Ecolabels for paints and varnishes have clauses restricting biocides and preservatives. Table 8 describes the criteria developed for restrictions of biocides in paints for different Ecolabels.

²⁸ <http://www.psf.mit.edu/esh/halosolv.html>

Table 8: Comparison of alternative ecolabel's criteria to biocides

Ecolabel	Criteria
Austrian Ecolabel - Paints, varnishes and wood sealant lacquers UZ01 (2010)	Used only for in-can preservation and only Government certified substances with specific limit values between 15 and 200 ppm.
German Blue Angel – Low emission paints RAL UZ12a (July 2010) – Varnishes & glazes	No micro biocides unless on German approved list and only for in-can preservation
Japanese Ecomark 126 – Paint Version 2.3 (2011)	Up to 0.5% of product weight

Clauses within the Austrian and German-based Ecolabels mirror the changes likely to be enacted within the scheduled update to the Biocide Regulation, due for release in 2013. The Directive will restrict the use and sale of certain biocides within Europe to those registered and authorised by relevant authorities within each country in the EU.²⁹

The wider scope for clauses defined in the Blue Angel and Austrian Ecolabel paints criteria are unsuitable for all the paints covered within the EU Ecolabel because of their use outdoors where biocides are necessary to prevent biofilms forming. Without biocides, the formation of biofilms will significantly reduce the lifetime of the paint. This may lead to an increase in the overall environmental impact due to necessary repaints. Therefore, a less stringent criterion for biocides is needed for products claiming antimicrobial action.

Bioaccumulation is a measure of the toxicological effect of substances within aquatic organisms: even if overall concentrations are low, prolonged exposure can give rise to toxic effects. Directive 1272/2008 defines the level at which a substance can be considered to bioaccumulate (or 'bioconcentrate') by determining the octanol/water partition coefficient, usually reported as a log K_{ow} . Within this Directive, log K_{ow} values equal to or greater than 4 can be considered 'bioaccumulative'. This value represents the potential to bioaccumulate, a more accurate (but usually unavailable) measure can be determined using the bioconcentration factor (BCF). A BCF in fish of ≥ 500 is indicative of the potential to bioconcentrate.

The suggested criterion below was presented in the 1st AHWG meeting and many stakeholders were positive:

Biocides

(i) The product may include biocides in order to preserve the product, and in the appropriate dosage for this purpose alone. These biocides shall be registered and authorized in the Biocide Product Regulation (BPD) scheme.

Assessment and verification: the applicant shall provide copies of the material safety data sheets of any preservatives added, together with information on their exact concentration in the product. The manufacturer or supplier of the preservatives shall provide information on the dosage necessary to preserve the product.

(ii) In accordance with Directive 67/548/EEC, Directive 1999/45/EC of the European Parliament and of the Council or Regulation (EC) No 1272/2008 substances or mixtures used as preservatives, that are classified as:

- *H400 Very toxic to aquatic life*
- *H410 Very toxic to aquatic life with long-lasting effects*

²⁹ <http://register.consilium.europa.eu/pdf/en/11/st05/st05032-re02.en11.pdf>

- H411 Toxic to aquatic life with long-lasting effects
- H412 Harmful to aquatic life with long-lasting effects
- H413 May cause long-lasting harmful effects to aquatic life

are permitted but only if their bioaccumulation potentials are characterised by $\log K_{ow}$ (\log octanol/water partition coefficient) $< 4,0$ or an experimentally determined bioconcentration factor (BCF) ≤ 500 .

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion.

Similar criterion but with different limits are currently used in other EU Ecolabel products. Many stakeholders have further suggested that the bioaccumulation limits within part (ii) could be strengthened to $\log K_{ow} < 3,0$ and $BCF \leq 100$ which are values used in other Ecolabel product groups³⁰. Criteria for other EU Ecolabel products such as laundry detergents use these values for $\log K_{ow}$ and BCF. However, there are obvious differences between detergents and paints. The nature of the product, function and use are completely different e.g. paints end up on a substrate and not in the wastewater like detergents except, perhaps, during the washing of brushes and rollers. A preliminary input from stakeholder was that even these low values can be achieved by the best performing paints. As the Ecolabelled products can comply with these restrictive limits these are also recommended for use. Additional feedback from manufacturers is asked

As presented in the preliminary criteria report it is suggested that a derogation request that breaches part (ii) above should be declined. That way part (ii) is used as a 'gate keeper' question during derogation requests for biocides whereas Part (i) could be included as a footnote within the derogations request to ensure that only the minimum amount of biocide is used. Furthermore requiring the authorisation of the products from the BPD is considered redundant as if the biocide is not authorised it cannot be used. Thus, the proposed text refers only to the registration of the substance.

(Part of Hazardous Substances criterion,

Note: the substances are presented as an example (non exhaustive list) s. also hazardous substances criterion)

USE	Chemical Composition Ingredient	CAS/ EINECS	Classification	Note
In can preservative	2-Methyl-2H-isothiazol-3-one	2682-20-4	R 22-23-34-43-50	1, 8, 9
	1,2-Benzisothiazol-3(2H)-one	2634-33-5	R 22-38-41-43-50	1, 8, 9
	Methyl-4-isothiazolin-3-one	2682-20-4	R34-37-43-50-24/25	1, 8, 9
	Tetrahydro-1,3,4,6-tetrakis(hydroxymethyl)imidazo[4,5-d]imidazol-2,5(1H,3H)-dion	5395-50-6	R43	2, 8
	Bronopol (INN) 2-bromo-2-nitropropane-1,3-diol	52-51-7	R21/22 R37/38-41, R50	2, 8, 9
	Mixture of: 5-chloro-2-methyl-4-isothiazolin-3-one [EC no. 247-500-7] and 2-methyl-2H-isothiazol-3-one [EC no. 220-239-6] (3:1)	55965-84-9	R23/24/25-34-43-50-53	3, 8, 9
	mixture of: 5-chloro-2-methyl-4-isothiazolin-3-one [EC no. 247-500-7] and 2-methyl-2H-isothiazol-3-one [EC no. 220-239-6] (3:1)	55965-84-9	R23/24/25-34-43-50-53	3, 8, 9
Dry film preservative	3-iodo-2-propinyl-butylcarbamate (IPBC)	55406-53-6	R 20/22-41-50	2, 8, 9
	Pyrithione zinc	13463-41-7	R 22-23-38-41-50	2, 8, 9
	2-Octyl-2H-isothiazol-3-one	26530-20-1	R 22, 23/24-34-43-50/53	1, 8, 9
	3-iodo-2-propinyl-butylcarbamate	55406-53-6	R 20/22-41-50	2, 8, 9
	Zinc oxide	1314-13-2	R 50/53	2, 8, 9
	1,2-Benzisothiazolin-3-one	2634-33-5	R 22-38-41-43-50	1, 8, 9

30 Establishing the ecological criteria for the award of the EU Ecolabel to detergents for dishwashers, (2011/263/EU)

	Zinc oxide	1314-13-2.	R 50/53	2, 8, 9
	Sodium polynaphthalene sulphonate	9084-06-4	R 52/53	2, 8, 9
	Diuron (ISO)	330-54-1	R22-40-48-48/22-50/53	2, 8, 9

Notes:

⁸: (i) The product may include biocides in order to preserve the product, and in the appropriate dosage for this purpose alone. . These biocides shall be registered in the Biocide Product Regulation (BPD) scheme.
(ii) In accordance with Directive 67/548/EEC, Directive 1999/45/EC of the European Parliament and of the Council or Regulation (EC) No 1272/2008 substances or mixtures used as preservatives are permitted but only if their bioaccumulation potentials are characterised by log Kow (log octanol/water partition coefficient) < 3,0 or an experimentally determined bioconcentration factor (BCF) ≤ 100.

4.2.10 Hazardous substances

The new Ecolabel Regulations [(EC) No 66/2010] aims to prevent the use of all chemicals classified as toxic, hazardous to the environment, carcinogenic, mutagenic or toxic for reproduction, and substances that are restricted under REACH regulations. The regulation stipulates:

6. The EU Ecolabel may not be awarded to goods containing substances or preparations/mixtures meeting the criteria for classification as toxic, hazardous to the environment, carcinogenic, mutagenic or toxic for reproduction (CMR), in accordance with Regulation (EC) No 1272/2008 of the European Parliament and of the Council of 16 December 2008 on classification, labelling and packaging of substances and mixtures, nor to goods containing substances referred to in Article 57 of Regulation (EC) No 1907/2006 of the European Parliament and of the Council of 18 December 2006 concerning the Registration, Evaluation, Authorisation and Restriction of Chemicals (REACH), establishing a European Chemicals Agency.

7. For specific categories of goods containing substances referred to in paragraph 6, and only in the event that it is not technically feasible to substitute them as such, or via the use of alternative materials or designs, or in the case of products which have a significantly higher overall environment performance compared with other goods of the same category, the Commission may adopt measures to grant derogations from paragraph 6. No derogation shall be given concerning substances that meet the criteria of Article 57 of Regulation (EC) No 1907/2006 and that are identified according to the procedure described in Article 59(1) of that Regulation, present in mixtures, in an article or in any homogeneous part of a complex article in concentrations higher than 0,1 % (weight by weight). Those measures, designed to amend non-essential elements of this Regulation, shall be adopted in accordance with the regulatory procedure with scrutiny referred to in Article 16(2).

There were significant concerns from stakeholders over the ability of the derogation system to enable a diverse pool of paints to meet the Ecolabel requirement. A large proportion of additives, including biocides and preservatives, surfactants, defoaming agents and other property-changing chemicals will not be allowed without derogations. The current consensus from industry is that there are no alternatives, and without these compounds the performance of the paints will be restricted. The advantage of this system is that large portions of the current criteria that address hazardous materials have been subsumed within this new criterion, simplifying the overall process.

The following derogations have been requested by manufacturers.

Derogation number a/a	USE	Chemical Composition Ingredient	CAS nr/ EINECS Nr / REACH registration Nr *	Classification	Maximum allowed concentration % w/w	Flagged from other stakeholders*
1	In can preservative	2-Methyl-2H-isothiazol-3-one	2682-20-4	R 22-23-34-43-50	0,008% - 0,1%	X
2		1,2-Benzisothiazol-3(2H)-one	2634-33-5	R 22-38-41-43-50	0,01% - 0,1%	X
3		Tetrahydro-1,3,4,6-tetrakis(hydroxymethyl)imidazo[4,5-d]imidazol-2,5(1H,3H)-dion	5395-50-6	R43	0.080%	X
4		bronopol (INN) 2-bromo-2-nitropropane-1,3-diol	52-51-7	R21/22 R37/38-41, R50	0.100%	X
5		mixture of: 5-chloro-2-methyl-4-isothiazolin-3-one [EC no. 247-500-7] and 2-methyl-2H-isothiazol-3-one [EC no. 220-239-6] (3:1)	55965-84-9	R23/24/25-34-43-50-53	0.002%	
6		Sodium N-(hydroxymethyl)glucinate	70161-44-3	Xi; R36, R43	0.050%	
7		3-iodo-2-propinyl-butylcarbamate (IPBC)	55406-53-6 EINECS: 259-627-5	R 20/22-41-50	0,3% 0,1% (concentration in antifungi paint)	
8		Pyrithione zinc	13463-41-7	R 22-23-38-41-50	0,1% (Exterior wall paint) 0,020% (Concentration as in film)	
9	Dry film preservative	terbutryn	886-50-0	Xn, Xi, N; R 22-43-50/53 Or Xn R22; Xn R48/22; Xi R43; R52/53 Or only R 50/53	0.100%	
10		4,5-Dichloro-2-octyl-3(2H)-isothiazolone	64359-81-5	C;R34, Xi;R37, Xi;R43, N;R50	0.700%	
11		Pyrithione zinc	13463-41-7	R 22-23-38-41-50	0,1% (Exterior wall paint) 0,020% (Concentration as in film)	
12		Cobalt, complexes de neodecanoate et de borate	68457-13-6	Xn, N, R38, R43, R50/53, R22	0.025%	X
13		3-iodo-2-propinyl-butylcarbamate (IPBC)	55406-53-6 EINECS: 259-627-5	R 20/22-41-50	0,3% 0,1% (concentration in antifungi paint)	
14		2-Octyl-2H-isothiazol-3-one	26530-20-1	R 22, 23/24-34-43-50/53	0.040%	X
15		zinc oxide	1314-13-2	R 50/53	0,005% to 2% (depending on category)	X
16		Sodium polynaphthalene sulphonate	9084-06-4	R 52/53	0.1%	X
17	Neutralising agent-pH	triethylamine	121-44-8	R11 - R22 - R23/24 - R35 - R41	0.200%	X
18		Alkanolamine	102-79-4	Xi: R41	2.000%	
19		Ammoniaque	1336-21-6	C, N, R34, R50	0.200%	
20		2-amino-2-methylpropanol	124-68-5	Xi: R36/38; R52/53	0.200%	

21	corrector	Ammonia	7664-41-7	R10; R23; R34; R50	0.065%	X
22		RTECS #: BO0875000				
		2,2'-iminodiethanol (DEA)	111-42-2	R22-48/22; R38-41	2.000%	X
23	Cobalt dryer	Cobalt bis(2-ethylhexanoate)	136-52-7	Xi; R43 N; R50/53	1%;	X
24		Fatty acids, tall-oil, cobalt salts	61789-52-4	Xn; R22 Xi; R43 , N; R51/53	0.500%	X
25		Neodecanoic acid	26896-20-8	R52/53	1.000%	X
26	Zinc dryer	Hexanoic acid, 2-ethyl-, zinc salt,BASIC	85203-81-2	R38, R51/53		X
27	antiskinning agent	2-butanone oxime ethyl methyl ketoxime / ethyl methyl ketone oxime	96-29-7	R40; R21; R41, R43	0.400%	X
28		Acideoctanoique, sel de zirconium	18312-04-4	Xi, R38	1.300%	X
29		lithium neodecanoate	27253-30-1	Xi, R38 Or Xi R38 ; R52/53	0.200%	X
30		Manganese salts	CAS 15956-58-8 or CAS 27253-32-3	Xi;R38.	4%	
31		Zirconium salt of 2-ethylhexanoic acid	22464-99-9	Xn, R20	0.600%	X
32	Other driers	Iron(1+), chloro[dimethyl-9,9-dihydroxy-3-methyl-2,4-di-(2-pyridyl-kN)-7-[(2-pyridinyl-kN)methyl]-3,7-diazabicyclo[3.3.1]nonane-1,5-dicarboxylate-kN3, kN7]-, chloride(1-)	478945-46-9	Xn; R22 Xn; R48/22 Xi; R43 R52/53	0.050%	x
33	UV protection filter (Light stabilizer)	Melange de : bis(2,2,6-tetramethyl-1-octyloxypiperidin-4-yl)-1,10-decanedioate; 1,8-bis((2,2,6,6-tetramethyl-4-((2,2,6,6-tetramethyl-1-octyloxypiperidin-4-yl)-decan-1,10-dioxy)l)piperidin-1-yl)oxy)octane	406-750-9	R53	0.60%	X
34		Bumetrizole	3896-11-5	R53	1.00%	X
35		reaction mass of α -3-(3-(2H-benzotriazol-2-yl)-5-tert-butyl-4-hydroxyphenyl)propionyl- ω -hydroxypoly(oxyethylene) and α -3-(3-(2H-benzotriazol-2-yl)-5-tert-butyl-4-hydroxyphenyl)propionyl- ω -3-(3-(2H-benzotriazol-2-yl)-5-tert-butyl-4-hydroxyphenyl)propionyloxypoly(oxyethylene)	EC: 400-830-7	R43 R51-53	0.990%	X
36		bis(1,2,2,6,6-pentamethyl-4-piperidyl) sebacate 70	41556-26-7	R43 R50/53	0.600%	X

		- 80 % Xi - N R43 - R50/53				
37		methyl 1,2,2,6,6-pentamethyl-4-piperidylsebacate	82919-37-7	R43-R50/53	0.200%	X
38		de 3-(3-(2h-benzotriazol-2-yl)5-(1,1-dimethylethyl)-4-hydroxyphenyl)propionates de c7-c9 alkyleramifie et lineaire	127519-17-9	R51/53	0.500%	X
39	Anticorrosive pigment (solid corrosive inhibitor).	zinc phosphate (2,5% ZnPO4)	ZnPO4: 7779-90-0	R50/53	8-10%	X
40		Zinc oxide	1314-13-2	R50/53	0,005% to 2% (depending on category)	X
41	Substrate Wetting agent / surface tension modifier	Polypropylene glycol alkylphenyl ether	9064-13-5	R43	3.000%	X
42		Polyoxyethylene isodecyl ether	61827-42-7	Xi; R41, Xn; R22	2.000%	X
43		Alcohols, C9-C11, ethoxylated	68439-46-3	Xi; R41	2.000%	X
44		Secondary Alcohols, C11-C15, ethoxylated	68131-40-8	Xi; R38, R41	2.000%	X
45		Secondary Alcohols, C12-C14, ethoxylated	84133-50-6	Xi; R41	2.000%	X
46		Alcohols, C16-C18, ethoxylated	68439-49-6	Xi, N, R50, R41 or Xn R22 ; Xi; R41	2.000%	X
47		Fatty alcohol ethoxylated	None	Xi; R41	2.000%	X
48		Alcohols, tallow,ethoxylated	61791-28-4	Xn; R22 ; Xi; R41	2.000%	X
49		Alcohols, C12-14,ethoxylated	68439-50-9	Xi; R41; N; R50	2.000%	X
50		Polyoxyethylenetridecyl ether phosphate	9046-01-9	Xi; R38 ; R41	2.000%	X
51		Poly(oxy-1,2-ethandediyl),a-isotridecyl-w-hydroxy-,phosphate	73038-25-2	Xi; R38 ; R41; R52/53	2.000%	X
52		Polyoxyethylenestearyl ether	9005-00-9	Xi; R41	2.000%	X
53		Isotridecanol, ethoxylated	9043-30-5 69011-36-5	Xn; R22 ; Xi; R41	2.000%	X
54		Alkyl polyglucoside	500-220-1	Xi; R41	2.000%	X
55		Tridecyl(polyethyleneoxy)ethanol	78330-21-9	Xn; R22 ; Xi; R41	2.000%	X
56		Sodium di-(2-ethylhexylic) sulfosuccinate	577-11-7	Xi; R38 ; R41	0.200%	X
57		2,4,7,9-tetramethyldec-5-yne-4,7-diol	126-86-3 / EINECS: 204-809-1	R 36, R 52/53	0.25%	X
58		Alkoxyated Alcohol	none	R52/53	2.000%	X
59		Silicon Resin	triethoxy(2,4,4-trimethylpentyl)silane	35435-21-3	R10 ; R52/53	3.000%

	Emulsion					
60		Hydrocarbures, C10-C13, n-alcane, isoalcanes, cycliques, < 2% aromatiques	01-2119457273-39-XXXX	Xn; R65, R66	2.000%	X
61	Solvent (in composition of some ingredients)	2-methylpropan-1-ol	78-83-1	R10 Xi; R37/38-R41 R67	2.000%	X
62		Petroleum distillates, solvent dewaxed heavy paraffinic (DMSO extract <3%)	64742-65-0	CAS N°64742-65-0 ; 72623-87-1 : These CAS N° stands for a Toxic R45 substance except the DMSO extract is below 3% (Note H,L)	2.000%	X
63		Hydrocarbures en c12-18	93924-45-9	Xn, R65, R66	0.060%	X
64		Ethylene glycol monobutyl ether	111-76-2	Xn; R20/21/22 - Xi; R36/38	1%	X
65		Lubricating oils (petroleum), C20-50, hydrotreated neutral oil-based	72623-87-1	CAS N°64742-65-0 ; 72623-87-1 : These CAS N° stands for a Toxic R45 substance except the DMSO extract is below 3% (Note H,L)	2.000%	X
66	Pigment	Nickel Titanium Yellow	8007-18-9	Heavy metal ?	2.000%	X
67	Silica in fillers	Derogation request for leucophyllite minerals containing crystalline silica classified STOT RE 1 and STOT RE 2		R48/25/24/23 or R48/20/21/22	0.500%	
68		crystalline silica classified STOT RE 1 or STOT RE 2 contained in fillers		R48/25/24/23 or R48/20/21/23	0.500%	
69		Heptanes (Naphtha),	092045-53-9	R11, 38, 51/53, 65, 67	0.020%	X
70		Complex alkanolamine	068784-47-4	R36/38	1.000%	X
71		Diethylene glycol (EC No. 2038722)	000111-46-6	R22	0.500%	X
72		iso-Propanol	000067-63-0	R11, 36, 67	0.020%	X

*Note: The requests of derogation were consulted within the stakeholders of the sub-AHWG for Hazardous substances. A limited number of stakeholders flagged these substances as they use alternatives.

None of these ingredients are flagged in Annex XIV of the REACH regulations, SVHC list, the SIN list or the Stockholm Convention POPs list.

Stakeholders had initially included the following additional substances as candidates for derogation but along the consultation these requests have been withdrawn.

2-dimethylaminoethanol N,N-dimethylethanolamine (DMEA)	108-01-0
Sodium hydroxide	1310-73-2
Cobalt polymer	
Cobalt carboxylate	68409-81-4
White spirit D60	64742-48-9

Moreover, related to STOT RE1 and STOT RE2 it should be highlighted that these refer to risks associated with inhalation of powders. In dry paint, crystalline silica will be embedded within the polymer binder of the paint, whilst in wet paint it will be in suspension and therefore this exposure pathway is not available. Regarding the use of crystalline silica which is classified as STOT RE 1 and STOT RE 2 (derogation Nr. 69-70) there was consensus among the members of the sub-AHWG on hazardous substances to grant the derogation. This is also proposed here though it should be highlighted that there could be a potential exposure when the paint is scratched off the wall (after its use life time). However, even then crystalline silica will be bounded together with the other ingredients and the substrate and this can lower the risk of inhalation.

The members of the sub-AHWG for the criterion on hazardous substances were consulted on the derogation requests. A limited number of members from both Competent Bodies and manufacturers challenged the derogation request for some of these substances. A stakeholder in particular stated that in their products these substances are not used. These flagged substances are indicated in the respective column of the above table. However, no additional information related to the alternatives used was provided. Moreover, it was also not possible to clarify which are the types of paints in which these substances are substituted. Stakeholders emphasized that the substances are not needed in every type of paint but might be necessary for specific uses. Based on these claims it is suggested that in derogation of a substance should explicitly include the reference to the type of paint for which its use is permitted. Further input of stakeholders regarding the type of paints for which alternatives are possible and the name of these alternatives are necessary in order to analyse these requests.

There are three possible options for determining the appropriate derogations for paints:

1. Use the extended list of derogations with additional restrictions that ensure that the current criterion (parts 6a, 6b, and 6c) are incorporated to limit the use of substances by risk phrase. Derogations for particular substances can be changed depending on the requirements of the paint. For example, the amount of biocides in paints could be stricter for indoor paint than in wet outside environments where mould and algae are a larger problem. Additional requirements for biocides (discussed in Section 4.2.9) and more stringent requirements based on CLP limits will also be included. These could serve as a 'gate keeper' for the derogated substances. Stakeholders have indicated it is possible to limit the hazardous substances within EU Ecolabelled paint to a threshold of 70% of the maximum allowable levels under CLP before the product is considered hazardous. Further variations in this can be managed through stakeholder discussion. Also, although the calculation is complex, it is currently mandated through the CLP regulations and should add little additional burden to the reporting costs associated with EU Ecolabel. On this after consultation with the industry it was highlighted that an implementation of such a CLP based requirement would need a transition time. Paint manufacturers are users of substances and mixtures and the CLP compliant information for all the raw materials used would be available in 2015 and not before. In addition, companies do not yet have the IT system that would allow them to do the classification calculations. Performing manually this calculation per ecolabelled paint would be an additional burden.

2. Reduce the list of derogated substances by removing those substances that have been challenged by Competent Bodies and other stakeholders. Several substances on the derogated list were queried by stakeholders who had specific concerns over their hazardous nature. Due to the number and complexity of derogated substances, it is beyond the scope of this project to determine if those requests are valid or more benign alternatives are available. A precautionary principle could be used to uphold these challenges; however, there is a significant risk that such an action may exclude a large proportion of paints from the EU Ecolabel. As a consequence the popularity (and thus the effectiveness) of the Ecolabel will be harmed.
3. Use the extended list initially with a further date (transition period) to move to a reduced list. This would allow manufacturers to phase-out problematic substances whilst still producing EU Ecolabelled paint.

Further discussions may be necessary to determine the appropriate course of action, but option 3 has been suggested within the text below.

There is ambiguity over the meaning of the term 'ingredient'. It can cover a mixture of substances as part of the paint manufacturer's formulation or the individual substances used in the production of precursors. A clear definition of this term is needed to enable fair and accurate assessment of the materials used in the manufacture of the paint. Stakeholders were in agreement and that a balance should be made to ensure that the information provided by the applicants enabled assessment of the environmental risks of the paint without proving too onerous. Previous discussions through an AHWG for the revision of this EU Ecolabel Criteria highlighted the issue of introducing an additional term "ingredients", which has not been formally defined. An appropriate alternative is to use the terms from the CLP Directive³¹; namely "Substance" and "Mixture" (formally preparation), which are defined as:

'substance' means a chemical element and its compounds in the natural state or obtained by any production process, including any additive necessary to preserve the stability of the product and any impurity deriving from the process used but excluding any solvent, which may be separated without affecting the stability of the substance or changing its composition;

'mixture' means a mixture or solution of two or more substances, which do not react.

Within the new dishwashing detergent criteria, the following text has been used to remove ambiguity:

...The risk phrases below generally refer to substances. However, for mixtures of enzymes and fragrances where information on substances may be difficult to obtain classification rules for mixtures may be applied.

A similar clause has been developed for this criterion.

Based on the submissions and the analysis performed above, the following amendments to the criterion are proposed.

Hazardous substances

According to Article 6(6) of the regulation No 66/2010 on EU Ecolabel, the product or any part of it thereof shall not contain substances or mixtures meeting the criteria for classification with the hazard classes or categories in accordance with Regulation (EC) no 1227/2008 specified below nor shall it contain substances referred to in Article 57 of REACH Regulation (EC) no 1907/2006. The risk phrases below generally refer to substances. However, for mixtures of substances where information on the substances is difficult to obtain, classification for rules of mixtures may be applied. The term mixture and substance are used as defined within the CLP Regulation (EC) No 1272/2008.

³¹Regulation (EC) No 1272/2008

Hazard Statement ¹	Risk Phrase ²
H300 Fatal if swallowed	R28
H301 Toxic if swallowed	R25
H304 May be fatal if swallowed and enters airways	R65
H310 Fatal in contact with skin	R27
H311 Toxic in contact with skin	R24
H330 Fatal if inhaled	R23; R26
H331 Toxic if inhaled	R23
H340 May cause genetic defects	R46
H341 Suspected of causing genetic defects	R68
H350 May cause cancer	R45
H350i May cause cancer by inhalation	R49
H351 Suspected of causing cancer	R40
H360F May damage fertility	R60
H360D May damage the unborn child	R61
H360FD May damage fertility. May damage the unborn child	R60-61
H360Fd May damage fertility. Suspected of damaging the unborn child	R60-63
H360Df May damage the unborn child. Suspected of damaging fertility	R61-62
H361f Suspected of damaging fertility	R62
H361d Suspected of damaging the unborn child	R63
H361fd Suspected of damaging fertility. Suspected of damaging the unborn child	R62-63
H362 May cause harm to breast fed children	R64
H370 Causes damage to organs	R39/23; R39/24; R39/25; R39/26; R39/27; R39/28
H371 May cause damage to organs	R68/20; R68/21; R68/22
H372 Causes damage to organs through prolonged or repeated exposure	R48/25; R48/24; R48/23
H373 May cause damage to organs through prolonged or repeated exposure	R48/20; R48/21; R48/22
H400 Very toxic to aquatic life	R50
H410 Very toxic to aquatic life with long-lasting effects	R50-53
H411 Toxic to aquatic life with long-lasting effects	R51-53
H412 Harmful to aquatic life with long-lasting effects	R52-53
H413 May cause long-lasting harmful effects to aquatic life	R53
EUH059 Hazardous to the ozone layer	R59
EUH029 Contact with water liberates toxic gas	R29
EUH031 Contact with acids liberates toxic gas	R31
EUH032 Contact with acids liberates very toxic gas	R32
EUH070 Toxic by eye contact	R39-41
Sensitising substances	
H334: May cause allergy or asthma symptoms or breathing difficulties if inhaled	R42
H317: May cause allergic skin reaction	R43

¹Regulation (EC) no 1272/2008 on classification, labelling and packaging of substances and mixtures, amending and repealing Directives 67/548/EEC and 1999/45/EC, and amending Regulation (EC) no 1907/2006

²Directive 67/548/EEC with adjustment to REACH according to Directive 2006/12/EC and Directive 1999/45/EC as amended.

Derogations: Following substances are exempt from this criterion

Derogation number a/a	USE	Chemical Composition Ingredient	CAS nr/ EINECS Nr / REACH registration Nr *	Classification	Requirement	Maximum allowed concentration % w/w	Only for a transition period of 2 years	Type of paint
1	In can preservative	2-Methyl-2H-isothiazol-3-one	2682-20-4	R 22-23-34-43-50	1, 5, 8, 9	0,1%	X	
2		1,2-Benzisothiazol-3(2H)-one	2634-33-5	R 22-38-41-43-50	1, 5, 8, 9	0,1%	X	
3		Tetrahydro-1,3,4,6-tetrakis(hydroxymethyl)imidazo[4,5-d]imidazol-2,5(1H,3H)-dion	5395-50-6	R43	2, 8, 9	0.080%	X	
4		bronopol (INN) 2-bromo-2-nitropropane-1,3-diol	52-51-7	R21/22 R37/38-41, R50	2, 5, 8, 9	0.100%	X	
5		mixture of: 5-chloro-2-methyl-4-isothiazolin-3-one [EC no. 247-500-7] and 2-methyl-2H-isothiazol-3-one [EC no. 220-239-6] (3:1)	55965-84-9	R23/24/25-34-43-50-53	2,3, 5, 8, 9	0.002%		
6		Sodium N-(hydroxymethyl)glucinate	70161-44-3	Xi; R36, R43	8, 9	0.050%		
7		3-iodo-2-propinyl-butylcarbamate (IPBC)	55406-53-6 EINECS: 259-627-5	R 20/22-41-50	8, , 9	0,3%		
8	Pyrithione zinc	13463-41-7	R 22-23-38-41-50	2, 5, 8, , 9	0,1%	X	Outdoor paint – façade coatings	
							All paints in film	
9	Dry film preservative	terbutryn	886-50-0	Xn, Xi, N; R 22-43-50/53 Or Xn R22; Xn R48/22; Xi R43; R52/53 Or only R 50/53	2, 5, 8, 9	0.100%		
10		4,5-Dichloro-2-octyl-3(2H)-isothiazolone	64359-81-5	C;R34, Xi;R37, Xi;R43, N;R50	5, 9	0.700%		
11		Pyrithione zinc	13463-41-7	R 22-23-38-41-50	2, 5, 8, 9	0,1%	X	Outdoor paint – façade coatings
								All paints in film
12		Cobalt, complexes de neodecanoate et de borate	68457-13-6	Xn, N, R38, R43, R50/53, R22	5, 9	0.025%	X	
13		3-iodo-2-propinyl-butylcarbamate (IPBC)	55406-53-6 EINECS: 259-627-5	R 20/22-41-50	2, 8, 5, 9	0,3%		
14	2-Octyl-2H-isothiazol-3-one	26530-20-1	R 22, 23/24-34-43-50/53	1, 2, 5, 8, 9	0.040%	X		

15		zinc oxide	1314-13-2	R 50/53	2, 5, 8, 9	2%	X	
16		Sodium polynaphthalene sulphonate	9084-06-4	R 52/53	2, 5, 8, 9	0.1%	X	
17	Neutralising agent-pH corrector	triethylamine	121-44-8	R11 - R22 - R23/24 - R35 - R41	2, 9	0.200%	X	
18		Alkanolamine	102-79-4	Xi: R41	9	2.000%		
19		Ammoniaque	1336-21-6	C, N, R34, R50	5, 9	0.200%		
20		2-amino-2-methylpropanol	124-68-5	Xi: R36/38; R52/53	5, 9	0.200%		
21		Ammonia	7664-41-7	R10; R23; R34; R50	2,5, 9	0.065%	X	
		RTECS #: BO0875000						
22		2,2'-iminodiethanol (DEA)	111-42-2	R22-48/22; R38-41	2, 9	2.000%	X	
23	Cobalt dryer	Cobalt bis(2-ethylhexanoate)	136-52-7	Xi; R43 N; R50/53	2,4,5, 9	1%;	X	
24		Fatty acids, tall-oil, cobalt salts	61789-52-4	Xn; R22 Xi; R43 , N; R51/53	4,5, 9	0.500%	X	
25		Neodecanoic acid	26896-20-8	R52/53	4,5, 9	1.000%	X	
26	Zinc dryer	Hexanoic acid, 2-ethyl-, zinc salt,BASIC	85203-81-2	R38, R51/53	5, 9		X	
27	Anti-skinning agent	2-butanone oxime ethyl methyl ketoxime / ethyl methyl ketone oxime	96-29-7	R40; R21; R41, R43	6, 9	0.400%	X	
28		Acideoctanoique, sel de zirconium	18312-04-4	Xi, R38	9	1.300%	X	
29		lithium neodecanoate	27253-30-1	Xi, R38 Or Xi R38 ; R52/53	5	0.200%	X	
30		Manganese salts	CAS 15956-58-8 or CAS 27253-32-3	Xi;R38.	9	4%		
31		Zirconium salt of 2-ethylhexanoic acid	22464-99-9	Xn, R20	9	0.600%	X	
32	Other driers	Iron(1+), chloro[dimethyl-9,9-dihydroxy-3-methyl-2,4-di-(2-pyridyl-kN)-7-[(2-pyridinyl-kN)methyl]-3,7-diazabicyclo[3.3.1]nonane-1,5-dicarboxylate-kN3, kN7]-, chloride(1-)	478945-46-9	Xn; R22 Xn; R48/22 Xi; R43 R52/53	2, 5	0.050%	X	
33	UV protection filtre (Light stabilizer)	Melange de : bis(2,2,6-tetramethyl-1-octyloxy piperidin-4-yl)-1,10-decanedioate; 1,8-bis((2,2,6,6-tetramethyl-4-((2,2,6,6-tetramethyl-1-octyloxy piperidin-4-yl)-decan-1,10-dioxy) piperidin-1-yl)oxy)octane	406-750-9	R53	5, 9	0.60%	X	Outdoor paints
34		Bumetrizole	3896-11-5	R53	5, 9	1.00%	X	Outdoor paints
35		reaction mass of α -3-(3-(2H-benzotriazol-2-yl)-	EC: 400-830-7	R43 R51-53	5, 9	0.990%	X	Outdoor

		hydroxypoly(oxyethylene) and α -3-(3-(2H-benzotriazol-2-yl)-5-tert-butyl-4-hydroxyphenyl)propionyl- ω -3-(3-(2H-benzotriazol-2-yl)-5-tert-butyl-4-hydroxyphenyl)propionyloxypoly(oxyethylene)						
36		bis(1,2,2,6,6-pentamethyl-4-piperidyl)sebacate 70 - 80 % Xi - N R43 - R50/53	41556-26-7	R43 R50/53	5, 9	0.600%	X	Outdoor paints
37		methyl 1,2,2,6,6-pentamethyl-4-piperidylsebacate	82919-37-7	R43-R50/53	5, 9	0.200%	X	Outdoor paints
38		de 3-(3-(2h-benzotriazol-2-yl)5-(1,1-dimethylethyl)-4-hydroxyphenyl)propionates de c7-c9 alkyleramifie et lineaire	127519-17-9	R51/53	5, 9	0.500%	X	Outdoor paints
39	Anticorrosive pigment (solid corrosive inhibitor).	zinc phosphate (2,5% ZnPO4)	ZnPO4: 7779-90-0	R50/53	5, 9	8-10%	X	
40		Zinc oxide	1314-13-2	R50/53	5, 9	2%	X	
41	Substrate Wetting agent / surface tension modifier	Polypropylene glycol alkylphenyl ether	9064-13-5	R43	9	3.000%	X	
42		Polyoxyethyleneisodecyl ether	61827-42-7	Xi; R41 & Xn; R22	9	2.000%	X	
43		Alcohols, C9-C11, ethoxylated	68439-46-3	Xi; R41	9	2.000%	X	
44		Secondary Alcohols, C11-C15, ethoxylated	68131-40-8	Xi; R38, R41	9	2.000%	X	
45		Secondary Alcohols, C12-C14, ethoxylated	84133-50-6	Xi; R41	9	2.000%	X	
46		Alcohols, C16-C18, ethoxylated	68439-49-6	Xi, N, R50, R41 or Xn R22 ; Xi; R41	5, 9	2.000%	X	
47		Fatty alcohol ethoxylated	None	Xi; R41	9	2.000%	X	
48		Alcohols, tallow,ethoxylated	61791-28-4	Xn; R22 ; Xi; R41	9	2.000%	X	
49		Alcohols, C12-14,ethoxylated	68439-50-9	Xi; R41; N; R50	5, 9	2.000%	X	
50		Polyoxyethylenetridecyl ether phosphate	9046-01-9	Xi; R38 ; R41	9	2.000%	X	
51		Poly(oxy-1,2-ethandediyl),a-isotridecyl-w-hydroxy-,phosphate	73038-25-2	Xi; R38 ; R41; R52/53	5, 9	2.000%	X	
52		Polyoxyethylenestearyl ether	9005-00-9	Xi; R41	9	2.000%	X	
53		Isotridecanol, ethoxylated	9043-30-5 69011-36-5	Xn; R22 ; Xi; R41	9	2.000%	X	
54		Alkyl polyglucoside	500-220-1	Xi; R41	9	2.000%	X	
55		Tridecyl(polyethyleneoxy)ethanol	78330-21-9	Xn; R22 ; Xi; R41	9	2.000%	X	
56		Sodium di-(2-ethylhexylic) sulfosuccinate	577-11-7	Xi; R38 ; R41	9	0.200%	X	
57		2,4,7,9-tetramethyldec-5-yne-4,7-diol	126-86-3 / EINECS: 204-809-1	R 36, R 52/53	5, 9	0.25%	X	
58		Alkoxyated Alcohol	None	R52/53	5, 9	2.000%	X	
59	Silicon Resin Emulsion	triethoxy(2,4,4-trimethylpentyl)silane	35435-21-3	R10 ; R52/53	5, 9	3.000%	X	
60	Solvent (in composition of some)	Hydrocarbures, C10-C13, n-alcanes, isoalcanes, cycliques, < 2% aromatiques	01-2119457273-39-XXXX	Xn; R65, R66	9	2.000%	X	

61		2-methylpropan-1-ol	78-83-1	R10 Xi; R37/38-R41 R67	9	2.000%	X	
62		Petroleum distillates, solvent dewaxed heavy paraffinic (DMSO extract <3%)	64742-65-0	CAS N°64742-65-0 ; 72623-87-1 : These CAS N° stands for a Toxic R45 substance except the DMSO extract is below 3% (Note H,L)	9	2.000%	X	
63		Hydrocarbures en c12-18	93924-45-9	Xn, R65, R66	9	0.060%	X	
64		Ethylene glycol monobutyl ether	111-76-2	Xn; R20/21/22 - Xi; R36/38	9	1%	X	
65		Lubricating oils (petroleum), C20-50, hydrotreated neutral oil-based	72623-87-1	CAS N°64742-65-0 ; 72623-87-1 : These CAS N° stands for a Toxic R45 substance except the DMSO extract is below 3% (Note H,L)	9	2.000%	X	
66	Pigment	Nickel Titanium Yellow	8007-18-9	Heavy metal	9	2.000%	X	
67		leucophyllite minerals containing crystalline silica classified STOT RE 1 and STOT RE 2		R48/25/24/23 or R48/20/21/22	9, 10	0.500%		All paints
68		crystalline silica classified STOT RE 1 or STOT RE 2 contained in fillers		R48/25/24/23 or R48/20/21/23	9, 10	0.500%		All paints
69		Heptanes (Naphtha),	092045-53-9	R11, 38, 51/53, 65, 67	5, 9	0.020%	X	
70		Complex alkanolamine	068784-47-4	R36/38	9	1.000%	X	
71		Diethylene glycol (EC No. 2038722)	000111-46-6	R22	9	0.500%	X	
72		iso-Propanol	000067-63-0	R11, 36, 67	9	0.020%	X	
73	Unreacted impurity	Volatile Aromatic Hydrocarbons	Various	Various	7			

Notes:

1. The sum of the total allowable concentration of these compounds is 0.05 % (w/w) before or after tinting (if applicable). For outdoor wood coatings the total allowable concentration shall not exceed 0.2 % (w/w).
2. The sum of the total allowable concentration of these compounds is 0.1% w/w).
3. The sum of the total allowable concentration of these compounds is 0.0015 % (w/w).
4. These compounds can only be used in alkyd paints and varnishes and up to a concentration not exceeding 0,05 % (w/w), measured as % of cobalt metal in the end product.
5. Substances or mixtures can have an allowable maximum concentration of 2% (w/ww/w) in the final paint formulation.
6. May be used in alkyd paints up to a limit of 0.3 % (w/w) in the final paint formulation.
7. Ingredients containing VAH may be added up to such a limit that the VAH content in the end product will not exceed 0,1 % (w/w). In this context volatile aromatic hydrocarbon (VAH) means any organic compound, as defined in Directive 2004/42/EC, having an initial boiling point less than or equal to 250 °C measured at a standard pressure of 101,3 kPa and having at least one aromatic nucleus in its developed structural formula.
8. The product may include biocides in order to preserve the product, and in the appropriate dosage for this purpose alone. These biocides shall be registered in the Biocide Product Regulation (BPD) scheme. Further, in accordance with Directive 67/548/EEC, Directive 1999/45/EC of the European Parliament and of the Council or Regulation (EC) No 1272/2008 substances or mixtures used as preservatives, that are classified as: H400, H410, H411, H412 and H413 are permitted but only if their bioaccumulation potentials are characterised by log Kow (log octanol/water partition coefficient) < 3,0 or an experimentally determined bioconcentration factor (BCF) ≤ 100.
9. After a transition period of two years the paint formulation shall not contain any hazardous substances, or combinations thereof, that result in the formulation being greater than 0.7 of the limits defined within PART A of directive 1999/45/EC and as required by the CLP regulation for marking dangerous substances.
10. Derogation is granted provided that the user before and during the paint use cannot come in contact with the substance in a dry form (e.g. the substance is within the liquid paint).

Hazardous substances (continue.)

The final product must not be labelled according to the hazard statements above.

Concentration limits for substances or mixtures which may be or have been assigned the hazard statements or risk phrase listed above, or which meet the criteria for classification in the hazard classes or categories listed in the table above, and concentration limits for substances meeting the criteria set out in Article 57(a), (b) or (c) of Regulation (EC) No 1907/2006, shall not exceed the generic or specific concentration limits determined in accordance with the Article 10 of Regulation (EC) No 1272/2008. Where specific concentration limits are determined, they shall prevail over the generic ones.

Concentration limits for substances meeting the criteria set out in Article 57(d), (e) or (f) of Regulation (EC) No 1907/2006 shall not exceed 0.1% weight by weight.

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion, together with a product material safety data sheet meeting the requirements of Annex II to the REACH Regulation and the quantity, in % (w/w), for all chemicals where derogations are sought. The applicant shall provide copies of the material safety data sheets of any preservatives added, together with information on their exact concentration in the product. The manufacturer or supplier of the preservatives shall provide information on the dosage necessary to preserve the product

4.2.11 Formaldehyde

Formaldehyde is toxic both by inhalation and ingestion, and minimising or eliminating its use is an important goal for improving human health (classification under CLP with R23/24/25, R34, R40, R43). Stakeholders agreed that complete elimination of formaldehyde would be beneficial but felt that it was impractical at this stage. Formaldehyde is used as an in-can preservative and complete removal will reduce the quality and lifetime of the paint (particularly in hot, Southern European countries).

Stakeholders, both before and during consultation, indicated that the current testing regime is inappropriate for determining the concentration of formaldehyde. The requirement to test all the ingredients, particularly dry ingredients is unnecessary. Formaldehyde is used primarily to preserve liquid ingredients and therefore requiring a test for dry ingredients presents additional cost burdens to applicants. The amount of free formaldehyde in the paint is calculated by summing each component. This does not allow for any further in-can reactions that may generate more or less formaldehyde.

Concerns were also raised that the current in-can calculation using VdL-RL 03 is not sufficiently accurate, necessitating a further test using HPLC where 'formaldehyde donors' may be present. Three modifications have been suggested:

- Remove the requirement to test solid ingredients. This is the simplest option but does not provide any assurances of actual in-can formaldehyde testing.
- Remove the requirement to test all ingredients and perform an in-can test using HPLC. This reduces the administration burden on the paint suppliers and ensures that the amount of formaldehyde is accurate, however, it does mandate a potentially expensive test.
- Test indoor air quality. This option is discussed further in Section 4.2.2.

The most appropriate and robust suggestion was to perform HPLC analysis on the final paint formulation. Due to the variation in different paint colours and tinting systems, a testing regime suggested by stakeholders determines the maximum amount of formaldehyde in the end product. Although there is an additional cost associated with the testing of each tinting pigment, this cost is likely to be less than that associated with the current regime that requires testing of all ingredients.

Stakeholders also requested additional points of clarification, in particular, that the tests should be performed on the in-can formulations to ensure that any formaldehyde present was in its most concentrated state. It was also requested that all laboratory tests conform to ISO 17025:2005. Additional wording has been provided to reflect these points.

It should be noted that this criterion does not overlap with the Hazardous Substances criterion because formaldehyde donors may not necessarily be considered hazardous.

Free formaldehydes shall not be added. Formaldehyde donors may only be added in such quantities as will ensure that the resulting total content after tinting (if applicable) of free formaldehyde will not exceed 0,001 % (w/w).

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion. In addition, the in-can concentration shall be determined using a standard based on High-Performance Liquid Chromatography using a testing laboratory certified to ISO 17025:2005. The applicant shall provide test results on the concentration of in-can formaldehyde on each paint colour, or where a tinting system is used, on the base paint, each colour tint, and the theoretical maximum on a tinted paint (i.e. a paint that contains the maximum amount of tint with the most amount of formaldehyde donor).

4.2.12 Phthalates

Phthalates are used as plasticisers in PVC giving the plastic desired physical properties. They can be also used in paints to alter the overall finish of the paint. Several phthalates have been shown to be endocrine inhibitors; this can cause cancerous tumours, birth defects, and other developmental disorders. Some phthalates are in the candidate list to be classified as Substances of Very High Concern (SVHC) which will lead based on article 6.7 of EC Ecolabel Regulation 66/2010 to be directly excluded from Ecolabel products. There is some guidance provided by the EU that certain phthalates, in particular di-isononyl phthalate (DINP) and diisodecyl phthalate (DIDP) have no associated health risks.³²

Many phthalates are excluded from several alternative ecolabels (US Green Seal and Austrian Ecolabel).³³ Within the paint industry, they are used in only a few applications and most stakeholders would welcome a ban in their use. As such the following criterion is suggested.

Intentional addition of phthalates is not permitted.

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion.

³² OJ C90/5 13.4.2006 (<http://www.didp-facts.com/upload/documents/document8.pdf>)

³³ Environ Health Perspect. 2007 March; 115(3): 390–396. Published online 2006 December 19

5 End of life

5.1 Unused paint disposal

5.1.1 Unused paint

As is discussed under the technical analysis in part 1 of this study, unused paint is a significant environmental concern. It adds significantly to the impact of the applied paint and causes environmental pollution from its improper disposal. A recent study³⁴, based on relatively old data, highlights the problem of unused paint in the UK. In the DIY market, an estimated 25% of all paint goes unused, whereas with trade this drops to 1.5%. Stakeholders disagree with these figures and believe that approximately 10% of all paint is wasted. This equates to approximately 700,000 te of unused paint wasted every year for the whole of Europe. Solvent-containing paint must be considered hazardous waste and undergo appropriate treatment. As is described within the LCC in the background report, hazardous waste disposal via incineration is approximately ten times the costs of non-hazardous waste.

A criterion to reduce the amount of wasted paint is important to reduce the overall environmental impact of the paint both in production and in treatment of the residuals. Unlike the manufacturing stage of paint where the ingredients and process are largely under the control of the manufacture, the responsibility at the end of life is shared among manufacturers, retailers, authorities and consumers. Therefore developing an appropriate criterion under the Ecolabel is more problematic.

There are different options and actions that can reduce the environmental impacts:

1. **Reuse.** Several schemes, mainly run as charitable organisations make use of unwanted paint selling either to the general public or for use within the social sector. Although unlikely to be operated directly by the manufacturers, support for such schemes could encourage more reuse and prevent waste. The largest hurdle for implementation is that collection and reuse throughout Europe is likely to be different between countries, which may be expensive to operate.
2. **Recycle or set minimum recycled content.** Recycling paint is an emerging technology whereby unused white paint is added to the base formulation. This reduces the amount of unused paint requiring disposal and can produce premium quality paint. The main concern is on the quality of the paint, particularly its anti-biocidal properties (has the old paint been contaminated?).
3. **Take-back for appropriate disposal.** As is described within the background report, solvent-containing waste paint must be treated as hazardous material and be sent for hazardous waste disposal (usually incineration). Although all countries should have the appropriate infrastructure to control this process, consumers may dispose of the waste paint through ordinary municipal waste streams (which could be damaging to the environment). Encouraging customers to return unwanted paint, for example to the point of sale, for appropriate disposal could be beneficial. There could, however, be problems in coordinating this requirement across Europe and the overall benefit may be limited.
4. **Combination of the above.** It is conceivable that developing the infrastructure for any of the above would facilitate the adoption of several reuse and recycling options. This would allow a manufacturer to decide the most appropriate method for controlling waste paint. It would however, be difficult to develop a flexible yet robust criterion to monitor this activity.

Alternative Ecolabels, in particular the Austrian Ecolabel, specify the development and implementation of a scheme to take-back, recycle and reuse unwanted paint. The French industry label 'RETOUR' is run by the French Environment Agency, ADÈME, to fulfil the requirements of their environmental code L541-10-4 which states that dangerous waste must be safely disposed of. The label is awarded to any suppliers of hazardous/industrial waste (including paint suppliers) who operate well-functioning and environmentally

³⁴ Paint and woodcare products - distribution and delivery, WRAP, 2011

well-performing take-back schemes for clients. The label guarantees a quality take-back service, and obliges the supplier to offer to take back any unused product when the client purchases new items. The unused paint is then safely disposed of within the existing EU regulations.

Manufacturers indicate that there would be a significant barrier to implementing a take-back or paint reuse scheme.

There is a clear environmental impact from unused paint. This extends to both disposal of the paint and also the impact of production of unused paint. There is significant resistance from manufacturers and producers to the implementation of a take-back or reuse scheme. They argue that the diversity of the waste collection regimes throughout Europe make developing a universal scheme impractical and schemes tailored to individual Member States are expensive. Conversely, there is some support from the Ecolabel Competent Bodies who recognise the environmental value of reuse. A criterion has been suggested that reflects these viewpoints.

Unused Paint

Applicants shall encourage paint reuse/recycling equivalent to at least 2%, by volume, of all their Ecolabelled paint sold per annum. This can be achieved by one or with combination of the following options:

- a) supporting reuse collection systems through third parties
- b) accepting unwanted paint for recycling or reuse
- c) supporting retailers with take-back systems.

The user should be respectively advised on the available options on how to deal with the unused paint.

Verification and assessment: The applicant shall either provide direct evidence of having a reuse scheme in place that reuses at least 2% by volume of paint per annum or provide evidence of substantial financial, logistical or physical support to a third party scheme that reuses 2%. It is not a requirement that the paint reused has obtained the EU Ecolabel. In addition, the applicant shall provide evidence through literature and packaging that instructs the end user where unused paint can be taken for reuse/recycling. These instructions should also be made available via the manufacturer website.

5.2 Packaging material

5.2.1 New Criterion: Packaging

Although relatively minor compared to reducing the amount of unused paint, additional criteria on minimising packaging waste would be environmentally beneficial. The literature review of LCAs performed within the background report concludes that the environmental impact of packaging is only a minor constituent compared to the production of the paint. The visibility of packaging waste is an important consideration.

The manufacture, use and disposal of packaging are important when considering both the volume of packaging waste (once the paint has been used) and to reduce the risk spillage to minimise paint waste and environmental damage. The use of reusable or lightweight packaging could also be considered.

There are three ways to reduce the environmental impact of the packaging:

1. Increasing the amount of recycled material within the paint pot
2. Decreasing the amount of material within the paint pot
3. Improving the usability and lifetime of the paint through changes in packaging design.

Mandating (1) within the EU Ecolabel appears to be achievable and could be readily introduced. To reduce the weight of packaging material (2), a modified criterion defined in the EU Ecolabel detergents criteria could be used:

$$WUR = \sum [(Wi + Ui)/(Di * ri)]$$

Where:

Wi = the weight (g) of the packaging component (i) including the label if applicable

Ui = the weight (g) of non-recycled (virgin) material in the packaging component (i). If the proportion of recycled material in the packaging component is 0% then $Ui = Wi$

Di = the number of functional units contained in the packaging component

(i). The functional unit = dosage in g/kg laundry. Note that the highest recommended dosage for each water hardness must be used in the WUR calculation.

ri = recycling figure, i.e. the number of times the packaging component (i) is used for the same purpose through a return or refill system.

r=1 if the packaging is not re-used for the same purpose. If the packaging is reused *r* is set to 1 unless the applicant can document a higher number.

However, information would be needed on the average weight of paint pots (and how this varies with size); whereas (3) could be used but is difficult to mandate and may stifle innovation. Without additional input, (1) is proposed as a new criteria.

Paint packaging

Plastic paint pots shall be made of a minimum 25% (w/w) post-consumer recycled material, be made of one polymer or be of compatible polymers for recycling and have the relevant ISO11469 marking.

This criterion does not apply to paint systems that deliver greater than 25 litres.

Verification and assessment: The applicant shall provide a declaration of compliance with this criterion along with evidence of marking.

6 General

6.1 Consumer information

The following information shall appear on the packaging or attached to the packaging:

- The use, substrate and conditions of use for which the product is intended. This shall include advice on preparatory work, etc., such as correct substrate preparation, advice on indoor use (where appropriate), or temperature
- Recommendations for cleaning tools and appropriate waste management (in order to limit water pollution). These recommendations shall be adapted to the type of product in question and field of application in question and may make use of pictograms if appropriate
- Recommendations concerning product storage conditions after opening (in order to limit solid waste), including safety advice if appropriate
- For darker coatings for which criterion 7(a) does not apply, advice is given concerning the use of the correct primer or base paint (if possible bearing the Community Eco-label)
- **(Indoor only)** — for thick decorative coatings a text informing that these are paints specially designed to give a three-dimensional decorative effect
- Text advising that unused paint requires specialist handling for safe environmental disposal and therefore it should not be thrown away with household refuse. The consumer should be informed on the provided and/or supported by the manufacture option for dealing the unused paint as given in criterion "unused paint".
- Recommendations on preventive protection measures for the painter. The following text (or equivalent text) shall appear on the packaging or attached to the packaging:
 - 'For more information as to why this product has been awarded the Flower please visit the web-site: <http://ec.europa.eu/environment/ecolabel>.'

Assessment and verification: A sample of the product packaging shall be provided when submitting the application, together with a corresponding declaration of compliance with this criterion as appropriate. The information in which is given advice on how to deal with the "unused paint" should also be available via the manufacturer website.

6.2 Information appearing on the Ecolabel

The current information appearing on the Ecolabel will need to be revised because the indoor and outdoor criteria are merged into a single document. In particular, a formalised system is needed to avoid customer confusion on the performance of the Ecolabel and the reason for the Ecolabel being awarded. This will partly be addressed within the structure of the new document and also the requirements for the labelling itself.

Box 2 of the Ecolabel shall contain the following text:

- Good performance for indoor use (where indoor criteria has been met)
- Good performance for outdoor use (where outdoor criteria has been met)
- Good performance for both indoor and outdoor use (where both indoor and outdoor criteria have been met)
- Minimised use of hazardous substances
- Low volatile organic compounds (VOCs).

Assessment and verification: The applicant shall provide a sample of the product packaging showing the label, together with a declaration of compliance with this criterion.

6.3 General comment

Stakeholders have requested a longer transition period between criteria to enable them to re-formulate as necessary and ready new dossier packs. It is proposed to discuss this issue in the 2nd AHWG as well on higher level in the EU Ecolabelling board as the decision taken there.

7 Criteria

Criteria aim

The criteria aim, in particular at promoting:

- products that have a lower environmental impact along their life cycle,
- products which contain a limited amount of hazardous substances
- products which emit a reduced amount of volatile organic compounds
- indoor products which ensure a higher indoor air quality
- the efficient use of the product and the minimization of waste

Criteria

Criteria are set for each of the following aspects:

1. Production phase -Raw material sourcing
2. Use phase
 - i) Efficiency in use
 - ii) Emissions during use
3. End of life phase
 - i) Unused paint disposal
 - ii) Packaging material
4. Consumer information- Information appearing on the Ecolabel

(1) Assessment and verification

(a) Requirements

The specific assessment and verification requirements are indicated within each criterion.

Where the applicant is required to provide declarations, documentation, analyses test reports or other evidence to show compliance with the criteria, it is understood that these may originate from the applicant and/or his supplier(s) and/or their supplier(s), et cetera, as appropriate.

Where possible, the testing should be performed by laboratories that meet the general requirements of EN ISO 17025 or equivalent.

Where appropriate, test methods other than those indicated for each criterion may be used if the competent body assessing the application accepts their equivalence.

Where appropriate, competent bodies may require supporting documentation and may carry out independent verifications. The competent bodies are recommended to take into account the implementation of recognised environmental management schemes, such as EMAS or EN ISO14001, when assessing applications and monitoring compliance with the criteria (*Note: it is not required to implement such management schemes*).

(b) Measurement thresholds

Unless otherwise indicated compliance with the ecological criteria is required for substances intentionally added, as well as for by-products and impurities from raw materials, the concentration of which equals or exceeds 0,010 % by weight of final formulation.

(2) Functional unit and reference flow

The reference flow for the functional unit of this product group is the amount of paint required to cover a 20 m² surface to a 98% opacity. The ingoing substances shall be also expressed in g of ingredient per amount of paint required to cover a 20 m² surface to a 98% opacity.

The exact formulation of the product (trade name, chemical name, CAS no.), the function and the form of all the ingoing substances (regardless of concentration) that are used by the applicant as well the ingoing quantity including and excluding water or solvent should be provided to the competent body. Any substance, including impurities, present in concentrations greater than 0,01 % (m/m) should be reported unless a lower concentration is specified elsewhere in the criteria.

Where ingredients are referred to in the criteria, this includes substances and preparations. The definitions of 'substances' and 'preparations' are given in the REACH Regulation (Regulation (EC) No 1907/2006 of the European Parliament and of the Council (1).

Safety data sheets for each ingoing substance shall be submitted to the competent body in accordance with Regulation (EC) No 1907/2006 of the European Parliament and of the Council.

Scope and definitions

The product group 'paints and varnishes' shall comprise both indoor and outdoor decorative paints and varnishes, woodstains and related products, as defined in paragraph 2, intended for use by do-it-yourself and professional users (please note that these are not industrial users).

This includes, inter alia, floor coatings and floor paints; products which are tinted by distributors at the request of amateur or professional decorators, tinting systems, decorative paints in liquid or paste formulas which may have been pre- conditioned, tinted or prepared by the manufacturer to meet consumer's needs, including wood paints, wood and decking stains, masonry coatings and metal finishes primers and undercoats of such product systems as defined within Directive 2004/42/CE Annex I 1.1.d and 1.1.g.

'Paint' means a pigmented coating material, in liquid or in paste or powder form, which when applied to a substrate, forms an opaque film having protective, decorative or specific technical properties.

'Varnish' means a clear coating material which when applied to a substrate forms a solid transparent film having protective, decorative or specific technical properties.

After application, the paint or varnish dries to a solid, adherent and protective coating.

'Decorative paints and varnishes' means paints and varnishes that are applied to buildings, their trim and fittings, for decorative and protective purposes. They are applied in-situ. While their main function is decorative in nature, they also have a protective role.

'Woodstains' (lasures) means coatings producing a transparent or semi-transparent (using substantially non-white pigment) film for decoration and protection of wood against weathering, which enables maintenance to be carried out easily.

'Tinting systems' is a method of preparing coloured paints by mixing a 'base' with coloured tints.

Masonry coatings are coatings that produce a decorative and protective film for use on concrete, (paintable) brickwork, blockwork, rendering, calcium silicate or fibre-reinforced cement. They are intended principally for exterior use, but may also be used internally, or on soffits and balcony ceilings.

The following definitions shall be used:

- Transparent contrast ratio < 90% at 120 μ
- Semi Transparent contrast ratio 90-98% at 120 μ
- Opaque contrast ratio >98% at 120 μ .

White and light coloured paints are those with a tri-stimulus (Y-value) >70%.

The product group shall not comprise:

- anti-fouling coatings
- wood preservation products
- coatings for particular industrial and professional uses, including heavy-duty coatings
- facade coatings
- powder coatings
- UV curable paint systems
- paints primarily intended for vehicles
- products that do not form film over the substrate.

White pigment

White pigment content (white inorganic pigments with a refractive index higher than 1,8): Paints shall have a white pigment content lower or equal to that described in the table below per m² of dry film, with 98 % opacity.

Wet scrub resistance	Indoor limit (g/m ²)	Outdoor limit (g/m ²)
Class 1	40	42
Class 2	36	38
Class 4	25	27

This requirement does not apply to varnishes and woodstains.

Assessment and verification: The applicant shall either provide a declaration of non-use or provide documentation showing the content of white pigments, the spreading rate and the assessment and verification criteria set out for the wet scrub resistance criterion, together with the detailed calculation showing compliance with this criterion.

Titanium dioxide

If the product contains more than 3.0 weight % of titanium dioxide, the emissions and discharges of wastes from the production of any titanium dioxide pigment used shall not exceed the following (as derived from the Reference Document on Best Available Technology for the Manufacture of Large Volume Inorganic Chemicals (BREF) (August 2007)):

The sulphate process:

- SO_x calculated as SO₂: 7.0 kg/ton TiO₂
- Sulphate waste: 500 kg/ton TiO₂.

The chloride process:

- If natural ore is used, 103 kg chloride waste/ton TiO₂
- If synthetic ore is used: 179 kg chloride waste /ton TiO₂
- If rutile ore is used: 329 kg chloride waste /ton TiO₂.

If more than one type of ore is used, the values will apply in proportion to the quantity of the individual ore types used.

Note:

SOx emissions only apply to the sulphate process.

For the avoidance of doubt, the Waste Framework Directive 2008/98/EC, article 3 defines waste. If the TiO₂ producer can satisfy article 5 (by-product production) of the Waste Framework Directive for its solid wastes then, the wastes shall be exempt.

Assessment and verification: The applicant shall either provide a declaration of non-use or provide the supporting documentation indicating the respective levels of emissions and discharges of wastes for these parameters, the titanium dioxide content of the product, the spreading rate, together with the detailed calculations showing compliance with this criterion.

USE

Efficiency in use

Dependant on the claims made on the properties of the paint, the following tests shall be undertaken.

Criteria	All	Outdoor ¹	Varnish	Floor covering and paint	Undercoat	Masonry paint
Spreading rate	X					
Wet scrub resistance	X					
Resistance to water			X			
Adhesion				X	X	X
Abrasion				X		X
Weathering		X				X
Water vapour permeability ²						X
Liquid water permeability ²						X
Fungal resistance ²						X
Crack bridging ²						X
Alkali resistance ²						X

Notes:

¹These are all products marketed as outdoor paints and include masonry paints

²Only required where marketing claims are made about the paints

Spreading rate

White paints and light-coloured paints (including finishes, primers, undercoats and/or intermediates) shall have a spreading rate (at a hiding power of 98 %) of at least 8m²per litre of product for indoor paints and 6m² for outdoor paints. For tinting systems, this criterion applies only to the white base (the base containing the most TiO₂). In cases where the white base is unable to achieve this requirement, the criterion shall be met after tinting the white base to produce the standard colour RAL 9010.

For all other bases used to produce tinted products — these are bases which as a rule contain less TiO₂, which are unable to achieve the requirement of at least 8m² per litre of product at a hiding power of 98 % — the criterion shall not apply. For paints that are a part of a tinting system, the applicant must advise the end-user on the product packaging and/or POS which shade or primer/undercoat (if possible bearing the Community Eco-label) should be used as a basecoat before applying the darker shade.

Primers with specific blocking/sealing, penetrating/binding properties and primers with special adhesion properties for aluminium and galvanised surfaces shall have a spreading rate (at a hiding power of 98 %) of at least 6m² per litre of product.

Thick decorative coatings (paints that are specially designed to give a three-dimensional decorative effect and are therefore characterised by a very thick coat) shall alternatively have a spreading power of 1m² per kg of product.

Elastomeric paints shall have a spreading rate (at a hiding power of 98 %) of at least 4m² per litre of product.

This requirement does not apply to varnishes, woodstains, floor coatings, floor paints, primers or any other transparent coatings.

Assessment and verification: The applicant shall provide a test report using the method ISO 6504/1 (Paints and varnishes — determination of hiding power — Part 1: Kubelka-Munk method for white and light-coloured paints) or 6504/3 (Part 3: determination of contrast ratio (opacity) of light-coloured paints at a fixed spreading rate), or for paints specially designed to give a three-dimensional decorative effect and characterised by a very thick coat the method NF T 30 073 (or equivalent). For bases used to produce tinted products not evaluated according to the abovementioned requirements, the applicant shall produce evidence of how the end-user will be advised to use a primer and/or grey (or other relevant shade) of undercoat before application of the product.

Wet scrub resistance

All paints shall have a wet scrub resistance as measured by EN 13300 and EN ISO 11998 of class 4 (not exceeding 70 microns after 200 cycles).

Paints (according to EN 13300) for which claims are made (whether on the product or in related marketing material) that they are brushable shall have a wet scrub resistance as measured by EN 13300 and EN ISO 11998 of class 2 (not exceeding 20 microns after 200 cycles).

Paints (according to EN 13300) for which claims are made (whether on the product or in related marketing material) that they are hard wearing, shall have a wet scrub resistance as measured by EN 13300 and EN ISO 11998 of class 1 (not exceeding 5 microns after 200 cycles).

Due to the large potential range of possible tinting colours, this criterion will be restricted to the testing of tinting bases.

Assessment and verification: The applicant shall provide a test report according to EN 13300 using the method EN ISO 11998 (Test for cleanability and scrub resistance).

Resistance to water

All varnishes, floor coatings and floor paints shall have a resistance to water, as determined by ISO 2812-3 such that after 24 hours' exposure and 16 hours' recovery no change of gloss or of colour occurs.

Assessment and verification: The applicant shall provide a test report using the method ISO 2812-3 (Paints and varnishes — determination of resistance to liquids — Part 3: Method using an absorbent medium).*

* this test procedure is due for revision during the lifetime of this criterion. If there is a substantive change to this procedure, a decision by the Competent Body Forum shall be taken on the appropriate test standard used.

Adhesion

Pigmented masonry primers shall score a pass in the EN 24624 (ISO 4624) pull-off test where the cohesive strength of the substrate is less than the adhesive strength of the paint, otherwise the adhesion of the paint must be in excess of a pass value of 1,5MPa.

Floor coatings, floor paints, floor undercoats, metal undercoats and wood undercoats shall score ≤ 2 in the EN 2409 test for adhesion.

Transparent primers are not included in this requirement

The applicant shall evaluate the primer and/or finish alone or both as part of a system [the system when tested shall concern products if possible labelled with the European Ecolabel (with the exception of systems designed for metal surfaces)]. When testing the finish alone this shall be considered the worst case scenario concerning adhesion.

Assessment and verification: The applicant shall provide a test report using the method EN ISO 2409 or EN 24624 (ISO 4624) as applicable

Abrasion

Floor coatings and floor paints shall have an abrasion resistance not exceeding 70 mg weight loss after 1000 test cycles with a 1000 g load and a CS10 wheel according to EN ISO 7784-2:2006.

Assessment and verification: The applicant shall provide a test report showing compliance with this criterion using the method EN ISO 7784-2:2006.

Weathering

Masonry finish paints and wood and metal finishes including varnishes shall be exposed to artificial weathering in apparatus including fluorescent UV lamps and condensation or water spray according to 11507:2007.

Masonry paints shall be exposed to test conditions for 1 000 hours, wood and metal finishes (including varnishes) shall be exposed to test conditions for 500 hours. Test conditions are: UVA 4h/60degC + humidity 4h/50degC.

Alternatively, wood finishes and wood varnishes may be exposed to weathering for 500 hours in the QUV accelerated weathering apparatus with cyclic exposure with UV(A) radiation and spraying according to EN 927-6.

According to ISO 7724-3:1984, the colour change of samples exposed to weathering shall not be greater than $\Delta E^* = 4$ and is not applicable to transparent varnishes and bases. To determine colour change of woodstains, a separate sample shall be prepared using an inert substrate and undergo weathering using a standard protocol outlined above.

Decrease samples in gloss for paints and varnishes exposed to weathering shall not be greater than 30 % of its initial value and shall be measured using ISO 2813. This is not applicable to matt-finish paints.

Chalking shall be tested using method EN ISO 4628-6:2007 on masonry finish coats and wood and metal finishes (where applicable) after the samples have been exposed to weathering. Coatings shall achieve a score of 1,5 or better (0,5 or 1,0) in this test. In the standard there are illustrated references.

The following parameters shall also be evaluated on masonry finish coats and wood and metal finishes after the samples have been exposed to weathering:

- Flaking according to ISO 4628-5:2003; flake density 2 or less, flake size 2 or less
- Cracking according to ISO 4628-4:2003; crack quantity 2 or less, crack size 3 or less
- Blistering according to ISO 4628-2:2003; blister density 3 or less, blister size 3 or less.

Due to the large number of possible tinting colours, these tests will be restricted to the base paint used.

Assessment and verification: The applicant shall provide test reports using either ISO11507:2007 according to the specified parameters or EN 927-6, or both (if relevant). The applicant shall provide test reports using EN ISO 4628-2, 4, 5, 6 where applicable. **Additionally, the applicant shall provide a test report in conformance to ISO 7724-3:1984* (where applicable).**

* this test procedure is due to be superseded by ISO 11664 during the lifetime of this criteria. If substantial changes to this procedure have been made, a decision by the Competent Body Forum shall be taken on the appropriate test standard to be used.

Water vapour permeability

Where claims are made that exterior masonry and concrete paints are breathable the paint shall be classified as class II (medium vapour permeability) or better according to the test method EN ISO 7783-2. Due to the large number of potential tinting colours, this criterion will be restricted to testing of the base paint; this requirement is not applicable to transparent primers.

Assessment and verification: The applicant shall provide a test report using methodology EN ISO 7783-2.

Liquid water permeability

Where claims are made that exterior masonry and concrete paints are water repellent or elastomeric, the coating shall be classified as class III (low liquid permeability) according to method EN 1062- 3:1999. Due to the large number of potential tinting colours, this criterion will be restricted to the testing of the base paint. All other masonry paints shall be classified as class II (medium liquid permeability) or better according to the test method EN 1062-3:1999.

Assessment and verification: The applicant shall provide a test report using methodology EN 1062-3:1999.

Fungal resistance

Where claims are made that masonry finish coatings have anti-fungal properties, the coating shall have a score of 2 or better (less than 10 % fungal coverage), as determined by method BS 3900:G6. Due to the large number of possible tinting colours, this criterion will be restricted to the testing of the base paint.

Assessment and verification: The applicant shall provide a test report using methodology BS 3900:G6.

Crack bridging

Where claims are made that masonry (or concrete) paint has elastomeric properties, it shall be at least classified as A1 at 23°C according to EN 1062-7:2004. Due to the large number of potential tinting colours, this criterion will be restricted to the testing of the base paint.

Assessment and verification: The applicant shall provide a test report using methodology DIN EN 1062-7:2004.

Alkali resistance

Masonry paints and primers shall show no noticeable damage when the coating is spotted for 24 hours with 10 % NaOH solution according to method ISO 2812-4:2007. The evaluation is done after 24 hours drying-recovery.

Assessment and verification: The applicant shall provide a test report using methodology ISO 2812-4:2007.

Corrosion resistance

-to be determined, criterion will cover only anti-corrosive coatings -

EMISSIONS DURING USE

Volatile Organic Compounds (VOC)

Volatile Organic Compounds content shall not exceed:

Description	VOC limits (g/l including water)
Indoor matt walls and ceilings (Gloss <25@60°)	10
Indoor glossy walls and ceilings (Gloss >25@60°)	40
Outdoor walls of mineral substrate	25
Indoor/Outdoor trim and cladding paints for wood and metal	80
Indoor trim varnishes and woodstains, including opaque woodstains	65
Outdoor trim varnishes and woodstains, including opaque woodstains	75
Indoor and Outdoor minimal build woodstains	50
Primers	10
Binding primers	10
One-pack performance coatings	80
Two-pack reactive performance coatings for specific end use such as floors	80
Decorative effect coatings	80
Anti-corrosion paints	80

In this context volatile organic compounds (VOC) means any organic compounds having an initial boiling point less than or equal to 250 °C measured at a standard pressure of 101,3 kPa as defined in Directive 2004/42/EC. The subcategories for paints and varnishes of the Directive are used for defining VOC limits. These values shall be measured at the point of application and must include any additional solvent added to the paint prior to application.

The total Semi Volatile Organic Compound (SVOC) shall be limited to 30 g/l including water. SVOCs are defined as organic substances or mixtures with a boiling range between 250 and 400°C.

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion. For all products the applicant shall indicate the VOC and SVOC content.

Indoor air quality

Each indoor paint shall undergo testing for Indoor air quality and meet Class A+ as defined within French Decree NOR : DEVL1104875A. This requirement is restricted to the lightest colour paint within a series or, in tinting systems, the base paint.

Verification and assessment: The applicant shall provide test results using the methodology described within NOR : DEVL1104875A.

Metals

The following heavy metals or their compounds shall not be used as an ingredient of the product or tint (if applicable) (whether as a substance or as part of any preparation used): cadmium, lead, chromium VI, mercury, arsenic, barium (excluding barium sulphate), selenium, antimony and cobalt.

It is accepted that ingredients may contain traces of these metals up to 0.01 deriving from impurities in the raw materials and can be present at these quantities for each metal for each ingredient.

Derogations for substances containing cobalt are described under the Hazardous Substances criterion.

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion as well as declarations from ingredient suppliers (where applicable).

Hazardous substances

According to Article 6(6) of the regulation No 66/2010 on EU Ecolabel, the product or any part of it thereof shall not contain substances or mixtures meeting the criteria for classification with the hazard classes or categories in accordance with Regulation (EC) no 1227/2008 specified below nor shall it contain substances referred to in Article 57 of REACH Regulation (EC) no 1907/2006. The risk phrases below generally refer to substances. However, for mixtures of substances where information on the substances is difficult to obtain, classification for rules of mixtures may be applied. The term mixture and substance are used as defined within the CLP Regulation (EC) No 1272/2008.

Hazard Statement ¹	Risk Phrase ²
H300 Fatal if swallowed	R28
H301 Toxic if swallowed	R25
H304 May be fatal if swallowed and enters airways	R65
H310 Fatal in contact with skin	R27
H311 Toxic in contact with skin	R24
H330 Fatal if inhaled	R23; R26
H331 Toxic if inhaled	R23
H340 May cause genetic defects	R46
H341 Suspected of causing genetic defects	R68
H350 May cause cancer	R45
H350i May cause cancer by inhalation	R49
H351 Suspected of causing cancer	R40
H360F May damage fertility	R60
H360D May damage the unborn child	R61
H360FD May damage fertility. May damage the unborn child	R60-61

H360Fd May damage fertility. Suspected of damaging the unborn child	R60-63
H360Df May damage the unborn child. Suspected of damaging fertility	R61-62
H361f Suspected of damaging fertility	R62
H361d Suspected of damaging the unborn child	R63
H361fd Suspected of damaging fertility. Suspected of damaging the unborn child	R62-63
H362 May cause harm to breast fed children	R64
H370 Causes damage to organs	R39/23; R39/24; R39/25; R39/26; R39/27; R39/28
H371 May cause damage to organs	R68/20; R68/21; R68/22
H372 Causes damage to organs through prolonged or repeated exposure	R48/25; R48/24; R48/23
H373 May cause damage to organs through prolonged or repeated exposure	R48/20; R48/21; R48/22
H400 Very toxic to aquatic life	R50
H410 Very toxic to aquatic life with long-lasting effects	R50-53
H411 Toxic to aquatic life with long-lasting effects	R51-53
H412 Harmful to aquatic life with long-lasting effects	R52-53
H413 May cause long-lasting harmful effects to aquatic life	R53
EUH059 Hazardous to the ozone layer	R59
EUH029 Contact with water liberates toxic gas	R29
EUH031 Contact with acids liberates toxic gas	R31
EUH032 Contact with acids liberates very toxic gas	R32
EUH070 Toxic by eye contact	R39-41
Sensitising substances	
H334: May cause allergy or asthma symptoms or breathing difficulties if inhaled	R42
H317: May cause allergic skin reaction	R43

¹Regulation (EC) no 1272/2008 on classification, labelling and packaging of substances and mixtures, amending and repealing Directives 67/548/EEC and 1999/45/EC, and amending Regulation (EC) no 1907/2006

²Directive 67/548/EEC with adjustment to REACH according to Directive 2006/12/EC and Directive 1999/45/EC as amended.

Derogations: Following substances are exempt from this criterion

Derogation number a/a	USE	Chemical Composition Ingredient	CAS nr/ EINECS Nr / REACH registration Nr *	Classification	Requirement	Maximum allowed concentration % w/w	Only for a transition period of 2 years	Type of paint		
1	In can preservative	2-Methyl-2H-isothiazol-3-one	2682-20-4	R 22-23-34-43-50	1, 5, 8, 9	0,1%	X			
2		1,2 Benzisothiazol-3(2H)-one	2634-33-5	R 22-38-41-43-50	1, 5, 8, 9	0,1%	X			
3		Tetrahydro-1,3,4,6-tetrakis(hydroxymethyl)imidazo[4,5-d]imidazol-2,5(1H,3H)-dion	5395-50-6	R43	2, 8, 9	0.080%	X			
4		bronopol (INN) 2-bromo-2-nitropropane-1,3-diol	52-51-7	R21/22 R37/38-41, R50	2, 5, 8, 9	0.100%	X			
5		mixture of: 5-chloro-2-methyl-4-isothiazolin-3-one [EC no. 247-500-7] and 2-methyl-2H-isothiazol-3-one [EC no. 220-239-6] (3:1)	55965-84-9	R23/24/25-34-43-50-53	2,3, 5, 8, 9	0.002%				
6		Sodium N-(hydroxymethyl)glucinate	70161-44-3	Xi; R36, R43	8 9	0.050%				
7		3-iodo-2-propinyl-butylcarbamate (IPBC)	55406-53-6 EINECS: 259-627-5	R 20/22-41-50	8, , 9	0,3%				
8		Pyrrithione zinc	13463-41-7	R 22-23-38-41-50	2, 5, 8, , 9	0,1%			Outdoor paint – façade coatings	
						0,020%			All paints in film	
9		Dry film preservative	terbutryn	886-50-0	Xn, Xi, N; R 22-43-50/53 Or Xn R22; Xn R48/22; Xi R43; R52/53 Or only R 50/53	2, 5, 8, 9	0.100%			
10			4,5-Dichloro-2-octyl-3(2H)-isothiazolone	64359-81-5	C;R34, Xi;R37, Xi;R43, N;R50	5, 9	0.700%			
11			Pyrrithione zinc	13463-41-7	R 22-23-38-41-50	2, 5, 8, 9	0,1%			Outdoor paint – façade coatings
							0,020%			All paints in film
12			Cobalt, complexes de neodecanoate et de borate	68457-13-6	Xn, N, R38, R43, R50/53, R22	5, 9	0.025%	X		
13	3-iodo-2-propinyl-butylcarbamate (IPBC)		55406-53-6 EINECS: 259-627-5	R 20/22-41-50	2, 8, 5, 9	0,3%				
14	2-Octyl-2H-isothiazol-3-one		26530-20-1	R 22, 23/24-34-43-50/53	1, 2, 5, 8, 9	0.040%	X			

15		zinc oxide	1314-13-2	R 50/53	2, 5, 8, 9	2%	X	
16		Sodium polynaphthalene sulphonate	9084-06-4	R 52/53	2, 5, 8, 9	0.1%	X	
17	Neutralising agent-pH corrector	triethylamine	121-44-8	R11 - R22 - R23/24 - R35 - R41	2, 9	0.200%	X	
18		Alkanolamine	102-79-4	Xi: R41	9	2.000%		
19		Ammoniaque	1336-21-6	C, N, R34, R50	5, 9	0.200%		
20		2-amino-2-methylpropanol	124-68-5	Xi: R36/38; R52/53	5, 9	0.200%		
21		Ammonia	7664-41-7	R10; R23; R34; R50	2,5, 9	0.065%	X	
		RTECS #: BO0875000						
22		2,2'-iminodiethanol (DEA)	111-42-2	R22-48/22; R38-41	2, 9	2.000%	X	
23	Cobalt dryer	Cobalt bis(2-ethylhexanoate)	136-52-7	Xi; R43 N; R50/53	2,4,5, 9	1%;	X	
24		Fatty acids, tall-oil, cobalt salts	61789-52-4	Xn; R22 Xi; R43 , N; R51/53	4,5, 9	0.500%	X	
25		Neodecanoic acid	26896-20-8	R52/53	4,5, 9	1.000%	X	
26	Zinc dryer	Hexanoic acid, 2-ethyl-, zinc salt,BASIC	85203-81-2	R38, R51/53	5, 9		X	
27	Anti-skinning agent	2-butanone oxime ethyl methyl ketoxime / ethyl methyl ketone oxime	96-29-7	R40; R21; R41, R43	6, 9	0.400%	X	
28		Acideoctanoique, sel de zirconium	18312-04-4	Xi, R38	9	1.300%	X	
29		lithium neodecanoate	27253-30-1	Xi, R38 Or Xi R38 ; R52/53	5	0.200%	X	
30		Manganese salts	CAS 15956-58-8 or CAS 27253-32-3	Xi;R38.	9	4%		
31		Zirconium salt of 2-ethylhexanoic acid	22464-99-9	Xn, R20	9	0.600%	X	
32	Other driers	Iron(1+), chloro[dimethyl-9,9-dihydroxy-3-methyl-2,4-di-(2-pyridyl-kN)-7-[[2-pyridinyl-kN)methyl]-3,7-diazabicyclo[3.3.1]nonane-1,5-dicarboxylate-kN3, kN7]-, chloride(1-)	478945-46-9	Xn; R22 Xn; R48/22 Xi; R43 R52/53	2, 5	0.050%	X	
33	UV protection filtre (Light stabilizer)	Melange de : bis(2,2,6-tetramethyl-1-octyloxypiperidin-4-yl)-1,10-decanedioate; 1,8-bis((2,2,6,6-tetramethyl-4-((2,2,6,6-tetramethyl-1-octyloxypiperidin-4-yl)-decan-1,10-dioxy)piperidin-1-yl)oxy)octane	406-750-9	R53	5, 9	0.60%	X	Outdoor paints
34		Bumetrizole	3896-11-5	R53	5, 9	1.00%	X	Outdoor paints
35		reaction mass of α -3-(3-(2H-benzotriazol-2-yl)-5-tert-butyl-4-hydroxyphenyl)propionyl- ω -	EC: 400-830-7	R43 R51-53	5, 9	0.990%	X	Outdoor paints

		hydroxypoly(oxyethylene) and α -3-(3-(2H-benzotriazol-2-yl)-5-tert-butyl-4-hydroxyphenyl)propionyl- ω -3-(3-(2H-benzotriazol-2-yl)-5-tert-butyl-4-hydroxyphenyl)propionyloxypoly(oxyethylene)						
36		bis(1,2,2,6,6-pentamethyl-4-piperidyl)sebacate 70 - 80 % Xi - N R43 - R50/53	41556-26-7	R43 R50/53	5, 9	0.600%	X	Outdoor paints
37		methyl 1,2,2,6,6-pentamethyl-4-piperidylsebacate	82919-37-7	R43-R50/53	5, 9	0.200%	X	Outdoor paints
38		de 3-(3-(2h-benzotriazol-2-yl)5-(1,1-dimethylethyl)-4-hydroxyphenyl)propionates de c7-c9 alkyleramifie et lineaire	127519-17-9	R51/53	5, 9	0.500%	X	Outdoor paints
39	Anticorrosive pigment (solid corrosive inhibitor).	zinc phosphate (2,5% ZnPO4)	ZnPO4: 7779-90-0	R50/53	5, 9	8-10%	X	
40		Zinc oxide	1314-13-2	R50/53	5, 9	2%	X	
41	Substrate Wetting agent / surface tension modifier	Polypropylene glycol alkylphenyl ether	9064-13-5	R43	9	3.000%	X	
42		Polyoxyethyleneisodecyl ether	61827-42-7	Xi; R41 & Xn; R22	9	2.000%	X	
43		Alcohols, C9-C11, ethoxylated	68439-46-3	Xi; R41	9	2.000%	X	
44		Secondary Alcohols, C11-C15, ethoxylated	68131-40-8	Xi; R38, R41	9	2.000%	X	
45		Secondary Alcohols, C12-C14, ethoxylated	84133-50-6	Xi; R41	9	2.000%	X	
46		Alcohols, C16-C18, ethoxylated	68439-49-6	Xi, N, R50, R41 or Xn R22 ; Xi; R41	5, 9	2.000%	X	
47		Fatty alcohol ethoxylated	None	Xi; R41	9	2.000%	X	
48		Alcohols, tallow,ethoxylated	61791-28-4	Xn; R22 ; Xi; R41	9	2.000%	X	
49		Alcohols, C12-14,ethoxylated	68439-50-9	Xi; R41; N; R50	5, 9	2.000%	X	
50		Polyoxyethylenetriodecyl ether phosphate	9046-01-9	Xi; R38 ; R41	9	2.000%	X	
51		Poly(oxy-1,2-ethandediyl),a-isotridecyl-w-hydroxy-,phosphate	73038-25-2	Xi; R38 ; R41; R52/53	5, 9	2.000%	X	
52		Polyoxyethylenestearyl ether	9005-00-9	Xi; R41	9	2.000%	X	
53		Isotridecanol, ethoxylated	9043-30-5 69011-36-5	Xn; R22 ; Xi; R41	9	2.000%	X	
54		Alkyl polyglucoside	500-220-1	Xi; R41	9	2.000%	X	
55		Tridecyl(polyethyleneoxy)ethanol	78330-21-9	Xn; R22 ; Xi; R41	9	2.000%	X	
56		Sodium di-(2-ethylhexylic) sulfosuccinate	577-11-7	Xi; R38 ; R41	9	0.200%	X	
57		2,4,7,9-tetramethyldec-5-yne-4,7-diol	126-86-3 / EINECS: 204-809-1	R 36, R 52/53	5, 9	0.25%	X	
58		Alkoxyated Alcohol	None	R52/53	5, 9	2.000%	X	
59	Silicon Resin Emulsion	triethoxy(2,4,4-trimethylpentyl)silane	35435-21-3	R10 ; R52/53	5, 9	3.000%	X	
60	Solvent (in composition of some ingredients)	Hydrocarbures, C10-C13, n-alcane, isoalcanes, cycliques, < 2% aromatiques	01-2119457273-39-XXXX	Xn; R65, R66	9	2.000%	X	

61		2-methylpropan-1-ol	78-83-1	R10 Xi; R37/38-R41 R67	9	2.000%	X	
62		Petroleum distillates, solvent dewaxed heavy paraffinic (DMSO extract <3%)	64742-65-0	CAS N°64742-65-0 ; 72623-87-1 : These CAS N° stands for a Toxic R45 substance except the DMSO extract is below 3% (Note H,L)	9	2.000%	X	
63		Hydrocarbures en c12-18	93924-45-9	Xn, R65, R66	9	0.060%	X	
64		Ethylene glycol monobutyl ether	111-76-2	Xn; R20/21/22 - Xi; R36/38	9	1%	X	
65		Lubricating oils (petroleum), C20-50, hydrotreated neutral oil-based	72623-87-1	CAS N°64742-65-0 ; 72623-87-1 : These CAS N° stands for a Toxic R45 substance except the DMSO extract is below 3% (Note H,L)	9	2.000%	X	
66	Pigment	Nickel Titanium Yellow	8007-18-9	Heavy metal	9	2.000%	X	
67		leucophyllite minerals containing crystalline silica classified STOT RE 1 and STOT RE 2		R48/25/24/23 or R48/20/21/22	9, 10	0.500%		All paints
68		crystalline silica classified STOT RE 1 or STOT RE 2 contained in fillers		R48/25/24/23 or R48/20/21/23	9, 10	0.500%		All paints
69		Heptanes (Naphtha),	092045-53-9	R11, 38, 51/53, 65, 67	5, 9	0.020%	X	
70		Complex alkanolamine	068784-47-4	R36/38	9	1.000%	X	
71		Diethylene glycol (EC No. 2038722)	000111-46-6	R22	9	0.500%	X	
72		iso-Propanol	000067-63-0	R11, 36, 67	9	0.020%	X	
73	Unreacted impurity	Volatile Aromatic Hydrocarbons	Various	Various	7			

Notes:

1. The sum of the total allowable concentration of these compounds is 0.05 % (w/w) before or after tinting (if applicable). For outdoor wood coatings the total allowable concentration shall not exceed 0.2 % (w/w).
2. The sum of the total allowable concentration of these compounds is 0.1% w/w).
3. The sum of the total allowable concentration of these compounds is 0.0015 % (w/w).
4. These compounds can only be used in alkyd paints and varnishes and up to a concentration not exceeding 0,05 % (w/w), measured as % of cobalt metal in the end product.
5. Substances or mixtures can have an allowable maximum concentration of 2% (w/ww/w) in the final paint formulation.
6. May be used in alkyd paints up to a limit of 0.3 % (w/w) in the final paint formulation.
7. Ingredients containing VAH may be added up to such a limit that the VAH content in the end product will not exceed 0,1 % (w/w). In this context volatile aromatic hydrocarbon (VAH) means any organic compound, as defined in Directive 2004/42/EC, having an initial boiling point less than or equal to 250 °C measured at a standard pressure of 101,3 kPa and having at least one aromatic nucleus in its developed structural formula.
8. The product may include biocides in order to preserve the product, and in the appropriate dosage for this purpose alone. These biocides shall be registered in the Biocide Product Regulation (BPD) scheme. Further, in accordance with Directive 67/548/EEC, Directive 1999/45/EC of the European Parliament and of the Council or Regulation (EC) No 1272/2008 substances or mixtures used as preservatives, that are classified as: H400, H410, H411, H412 and H413 are permitted but only if their bioaccumulation potentials are characterised by log Kow (log octanol/water partition coefficient) < 3,0 or an experimentally determined bioconcentration factor (BCF) ≤ 100.
9. After a transition period of two years the paint formulation shall not contain any hazardous substances, or combinations thereof, that result in the formulation being greater than 0.7 of the limits defined within PART A of directive 1999/45/EC and as required by the CLP regulation for marking dangerous substances.
10. Derogation is granted provided that the user before and during the paint use cannot come in contact with the substance in a dry form (e.g. the substance is within the liquid paint).

Hazardous substances (continue.)

The final product must not be labelled according to the hazard statements above.

Concentration limits for substances or mixtures which may be or have been assigned the hazard statements or risk phrase listed above, or which meet the criteria for classification in the hazard classes or categories listed in the table above, and concentration limits for substances meeting the criteria set out in Article 57(a), (b) or (c) of Regulation (EC) No 1907/2006, shall not exceed the generic or specific concentration limits determined in accordance with the Article 10 of Regulation (EC) No 1272/2008. Where specific concentration limits are determined, they shall prevail over the generic ones.

Concentration limits for substances meeting the criteria set out in Article 57(d), (e) or (f) of Regulation (EC) No 1907/2006 shall not exceed 0.1% weight by weight.

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion, together with a product material safety data sheet meeting the requirements of Annex II to the REACH Regulation and the quantity, in % (w/w), for all chemicals where derogations are sought. The applicant shall provide copies of the material safety data sheets of any preservatives added, together with information on their exact concentration in the product. The manufacturer or supplier of the preservatives shall provide information on the dosage necessary to preserve the product

Formaldehyde

Free formaldehydes shall not be added. Formaldehyde donors may only be added in such quantities as will ensure that the resulting total content after tinting (if applicable) of free formaldehyde will not exceed 0,001% (m/m).

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion. In addition, the in-can concentration shall be determined using a standard based on High-Performance Liquid Chromatography using a testing laboratory certified to ISO 17025:2005. The applicant shall provide test results on the concentration of in-can formaldehyde on each paint colour, or where a tinting system is used, on the base paint, each colour tint, and the theoretical maximum on a tinted paint (i.e. a paint that contains the maximum amount of tint with the most amount of formaldehyde donor).

Phthalates

Intentional addition of phthalates is not permitted.

Assessment and verification: The applicant shall provide a declaration of compliance with this criterion.

END OF LIFE

Unused Paint

Applicants shall encourage paint reuse/recycling equivalent to at least 2%, by volume, of all their Ecolabelled paint sold per annum. This can be achieved by one or with combination of the following options:

- a) supporting reuse collection systems through third parties
- b) accepting unwanted paint for recycling or reuse
- c) supporting retailers with take-back systems.

The user should be respectively advised on the available options on how to deal with the unused paint.

Verification and assessment: The applicant shall either provide direct evidence of having a reuse scheme in place that reuses at least 2% by volume of paint per annum or provide evidence of substantial financial, logistical or physical support to a third party scheme that reuses 2%. It is not a requirement that the paint reused has obtained the EU Ecolabel. In addition, the applicant shall provide evidence through literature and packaging that

instructs the end user where unused paint can be taken for reuse/recycling. These instructions should also be made available via the manufacturer website.

Recycled content

Plastic paint pots shall be made of a minimum 25% (m/m) post-consumer recycled material, be made of one polymer or be of compatible polymers for recycling and have the relevant ISO11469 marking.

This criterion does not apply to paint systems that deliver greater than 25 litres.

Verification and assessment: The applicant shall provide a declaration of compliance with this criterion along with evidence of marking.

GENERAL

Consumer information

The following information shall appear on the packaging or attached to the packaging:

- The use, substrate and conditions of use for which the product is intended. This shall include advice on preparatory work, etc., such as correct substrate preparation, advice on indoor use (where appropriate), or temperature
- Recommendations for cleaning tools and appropriate waste management (in order to limit water pollution). These recommendations shall be adapted to the type of product in question and field of application in question and may make use of pictograms if appropriate
- Recommendations concerning product storage conditions after opening (in order to limit solid waste), including safety advice if appropriate
- For darker coatings for which criterion 7(a) does not apply, advice is given concerning the use of the correct primer or base paint (if possible bearing the Community Eco-label)
- **(Indoor only)** — for thick decorative coatings a text informing that these are paints specially designed to give a three-dimensional decorative effect
- Text advising that unused paint requires specialist handling for safe environmental disposal and therefore it should not be thrown away with household refuse. The consumer should be informed on the provided and/or supported by the manufacture option for dealing the unused paint as given in criterion "unused paint".
- Recommendations on preventive protection measures for the painter. The following text (or equivalent text) shall appear on the packaging or attached to the packaging:
'For more information as to why this product has been awarded the Flower please visit the web-site:
[http://ec.europa.eu/environment/ecolabel.](http://ec.europa.eu/environment/ecolabel)'

Assessment and verification: A sample of the product packaging shall be provided when submitting the application, together with a corresponding declaration of compliance with this criterion as appropriate. The information in which is given advice on how to deal with the "unused paint" should also be available via the manufacturer website.

Information appearing on the Ecolabel

Box 2 of the Ecolabel shall contain the following text:

- Good performance for indoor use (where indoor criteria has been met)
- Good performance for outdoor use (where outdoor criteria has been met)
- Good performance for both indoor and outdoor use (where both indoor and outdoor criteria have been met)
- Minimised use of hazardous substances
- Low volatile organic compounds (VOCs).

Assessment and verification: The applicant shall provide a sample of the product packaging showing the label, together with a declaration of compliance with this criterion.